


Catalysis for polymerization

Synthesis of
new polymers

Tailoring of **new monomers**
Multistep organic synthesis

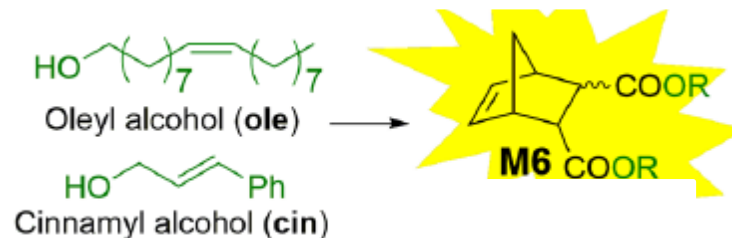


Development of **new catalysts** able to
polymerize in a new fashion
simple and commercially available monomers

Precision Polymerization


G. Chen, X. S. Ma, Z. Guan *J. Am. Chem. Soc.* 2003, 125, 6697.

Catalysis for polymerization

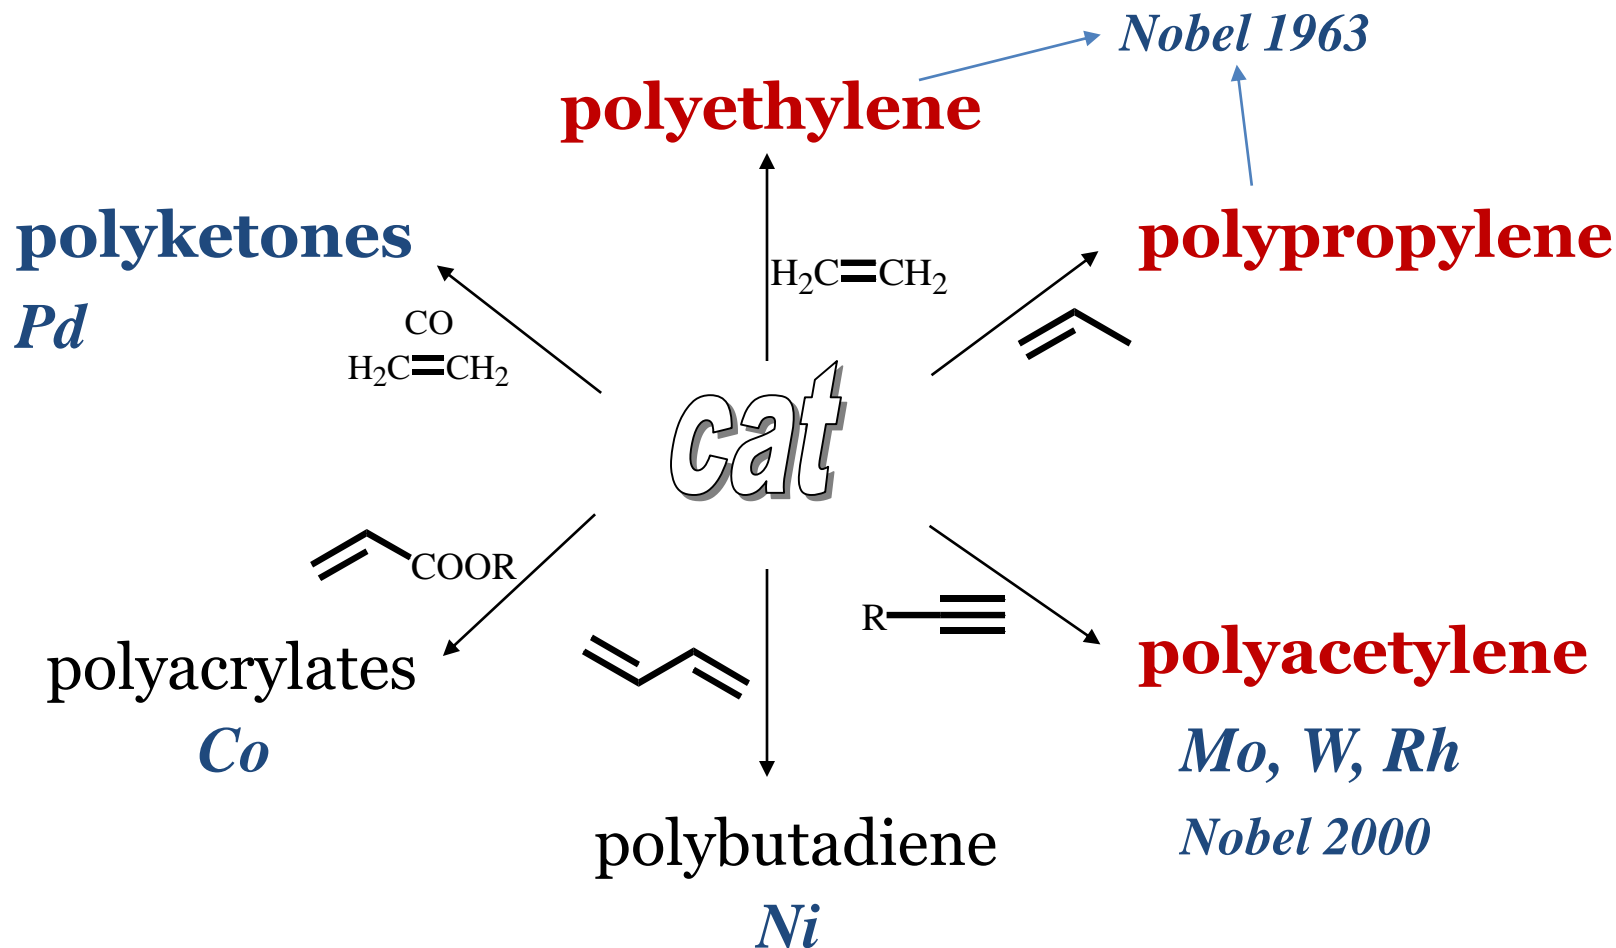

¹S. Kobayashi, *Catalysis in Precision Polymerisation* **1997**, Ed. Wiley.

Polyacetylene and substituted polyacetylene

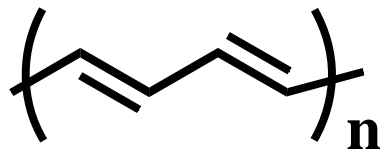


The polymers are featured by **conjugated** C-C double bonds. Thus, they show peculiar properties not found in polyolefins. The most important is the conductivity of electricity.

Polyacetylene is a **black solid, unstable** in air. It behaves like a **semiconductor**, but when properly **dopped** with AsF_5 or I_2 it shows the **conductivity** like a metal.


Substituted polyacetylenes have different **colors** depending on the number and the nature of the substituents; they are **soluble** in common organic solvents, they are **stable** in air for long time and they are **insulators**.

Catalysis for polymerization

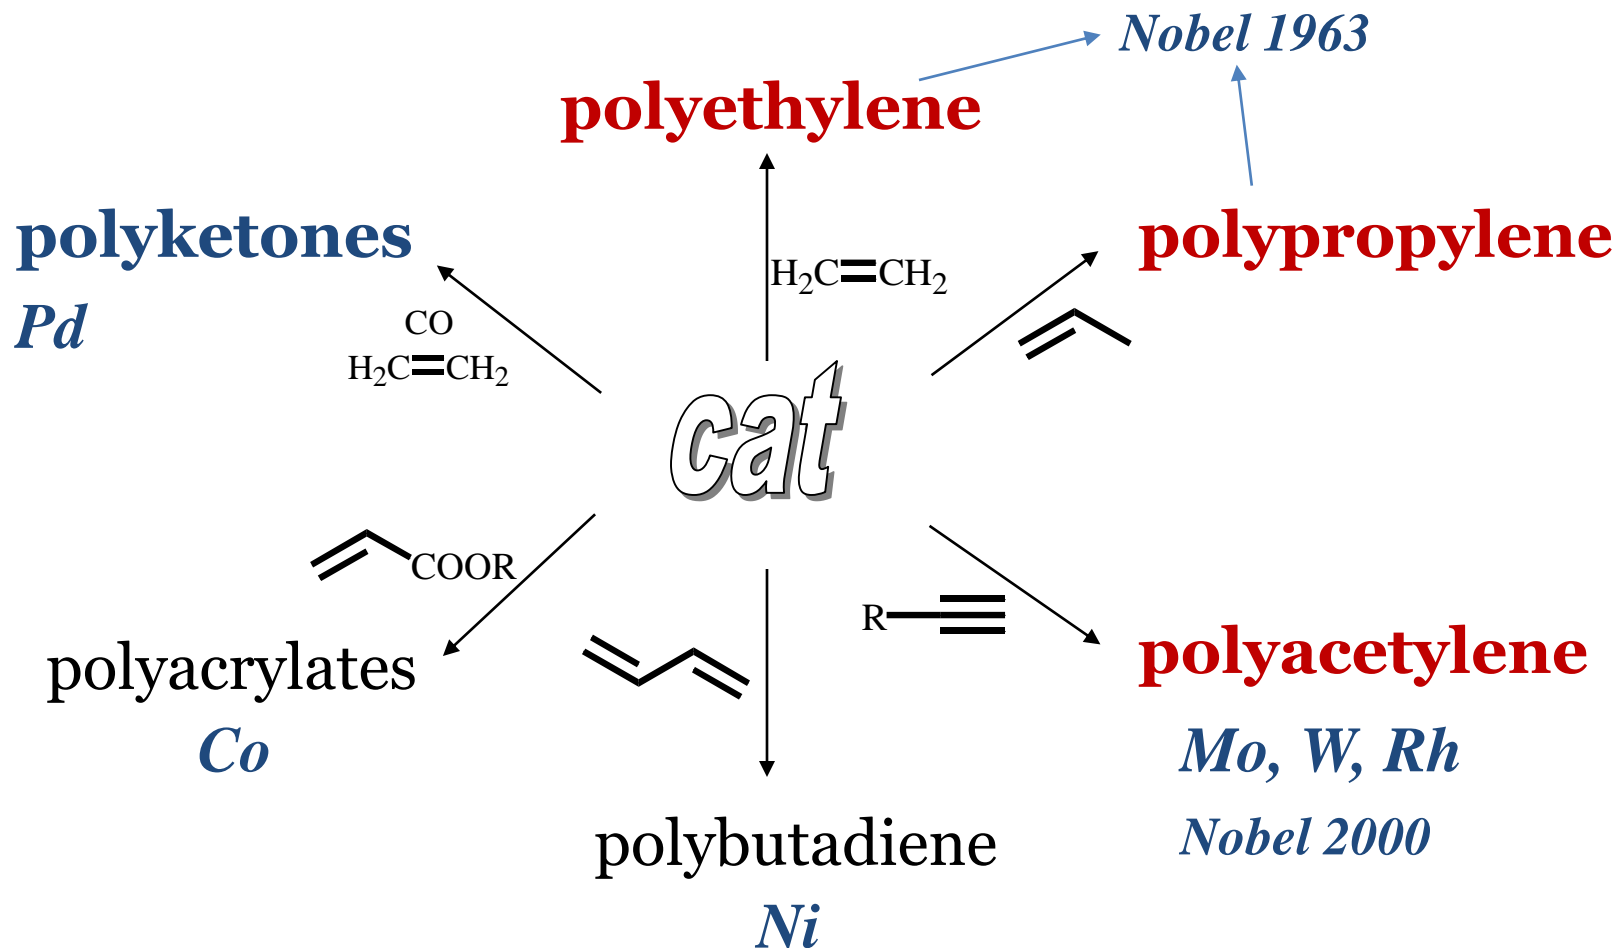

¹S. Kobayashi, *Catalysis in Precision Polymerisation* **1997**, Ed. Wiley.

CO/terminal alkene copolymerization

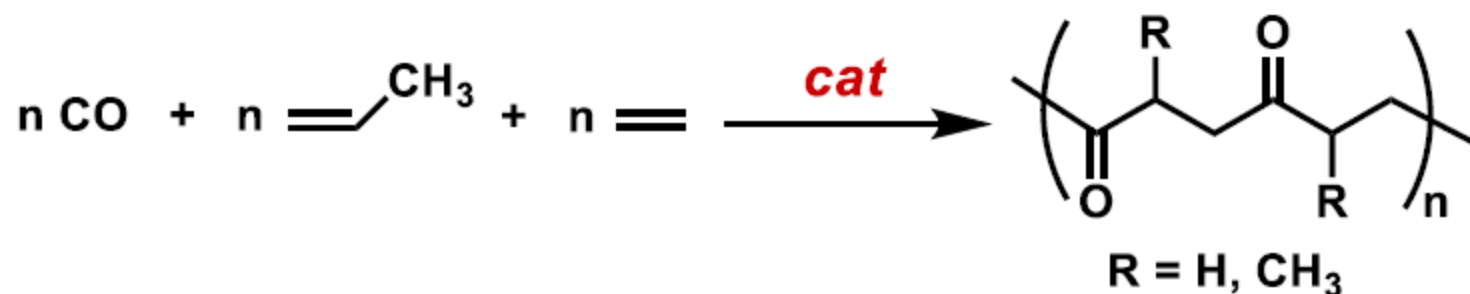

Commercialized by Shell Chemicals

Drent, E. et al. *J. Organomet. Chem. Soc.* **1991**, 417, 235; Drent, E. et al. *Chem. Rev.*, **1996**, 96, 663; Alperwicz, N., *Chem. Week.* **1995**, 22.

Innovative engineering plastics we have dreamed of

POKETONE is a new eco-friendly thermoplastic made of CO and olefins. With its unique balance of excellent properties, it will bring you various innovations for diverse applications.




Commercialized by Hyosung


http://www.poly-ketone.com/utl/web/mediadownload.do?subpath=/download/catalogEn/poketone_catalogue2017_en.pdf

Synthesis of copolymers

CO/alkene Copolymers

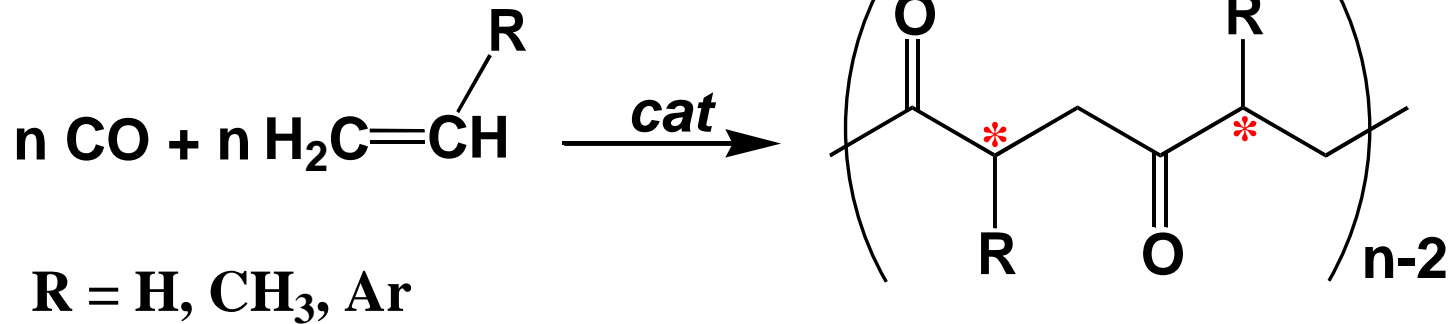


Ethylene/polar vinyl monomers Copolymers

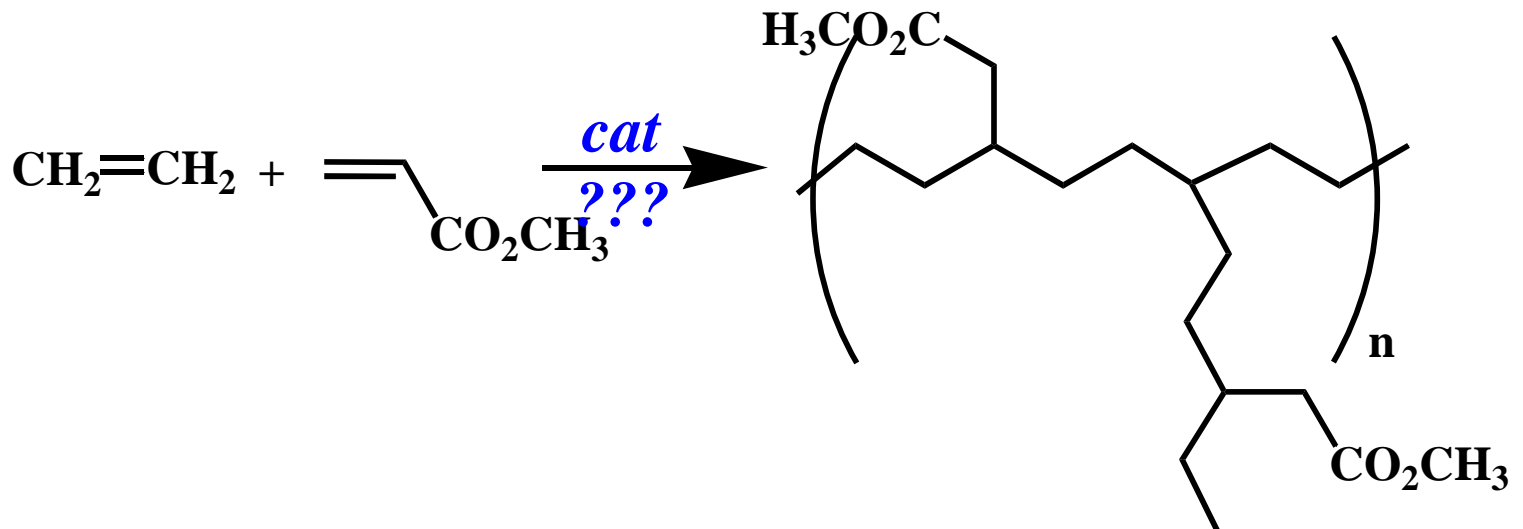

Ring-opening metathesis polymerization


ROMP

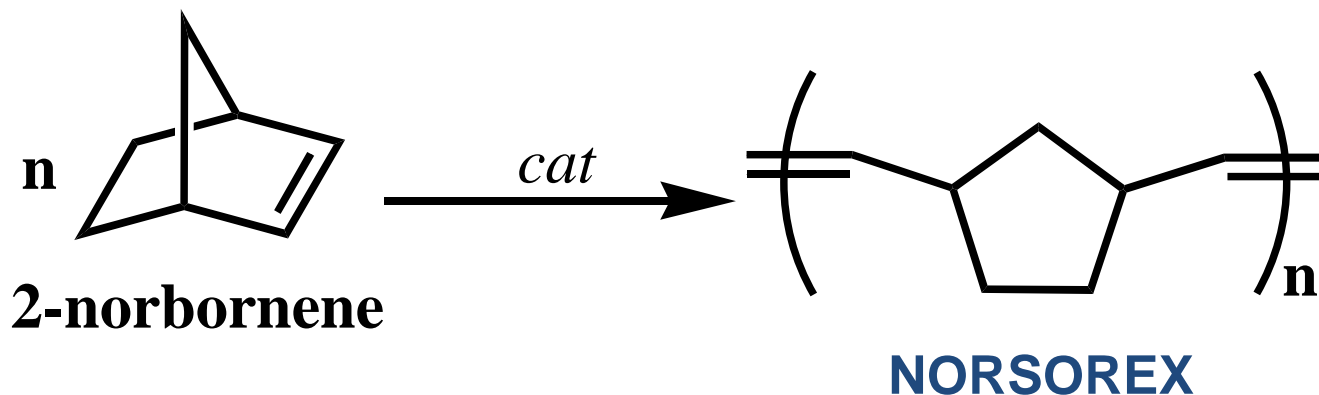


Polymerization with retaining of the functional groups.

<https://youtu.be/KzzkYYYPNxl>


Plastic: is the abbreviative of **thermoplastic**, a type of material that can be melted when heated and solidified when cooled. This process can be repeated almost indefinitely.

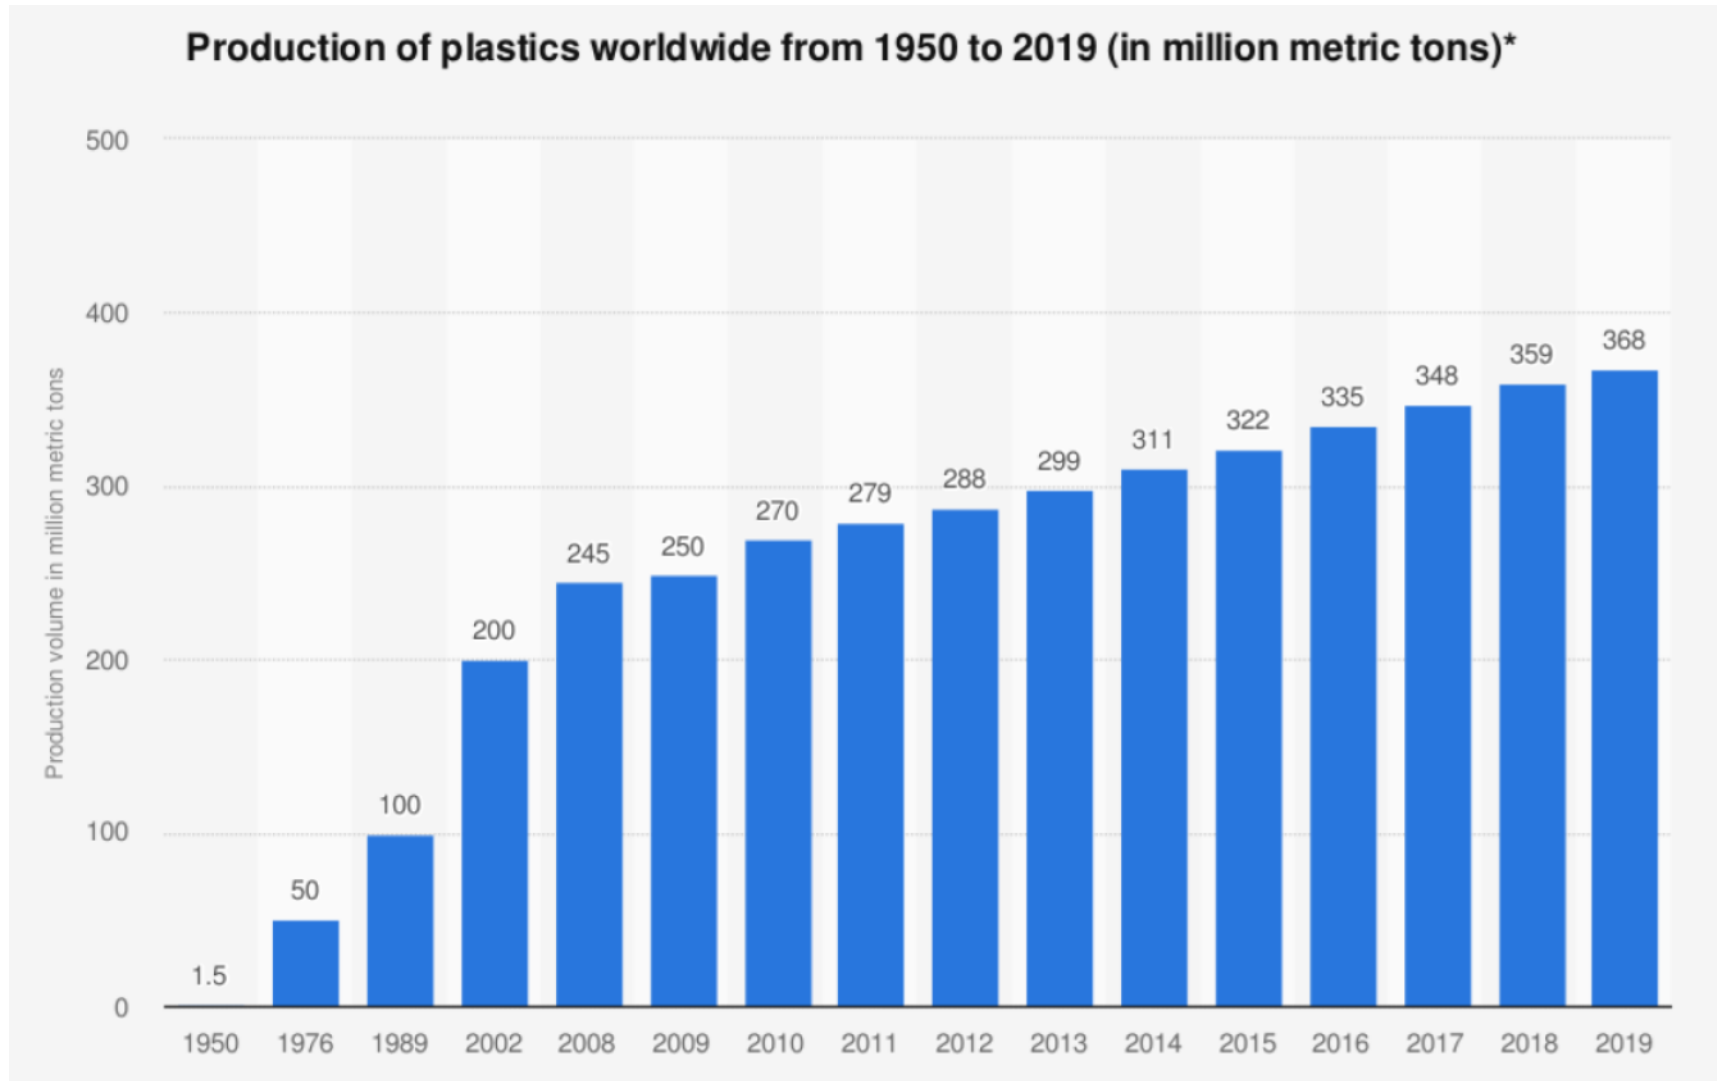

Global primary plastic production according to polymer type

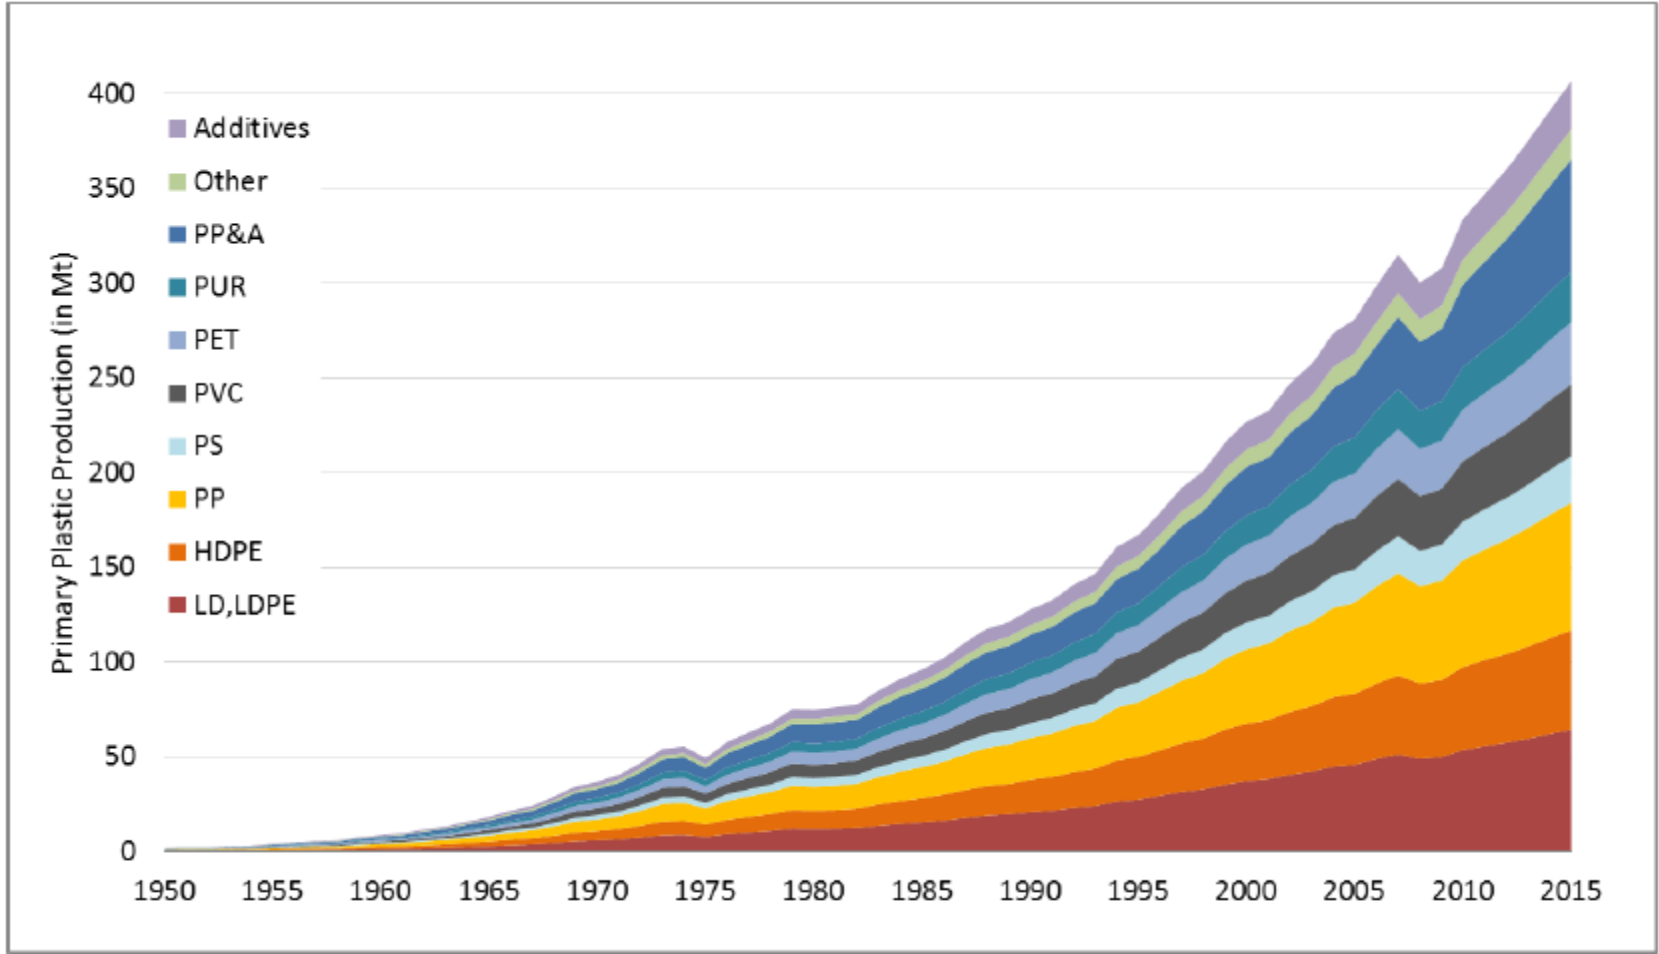


The problem of polyolefin environmental pollution.

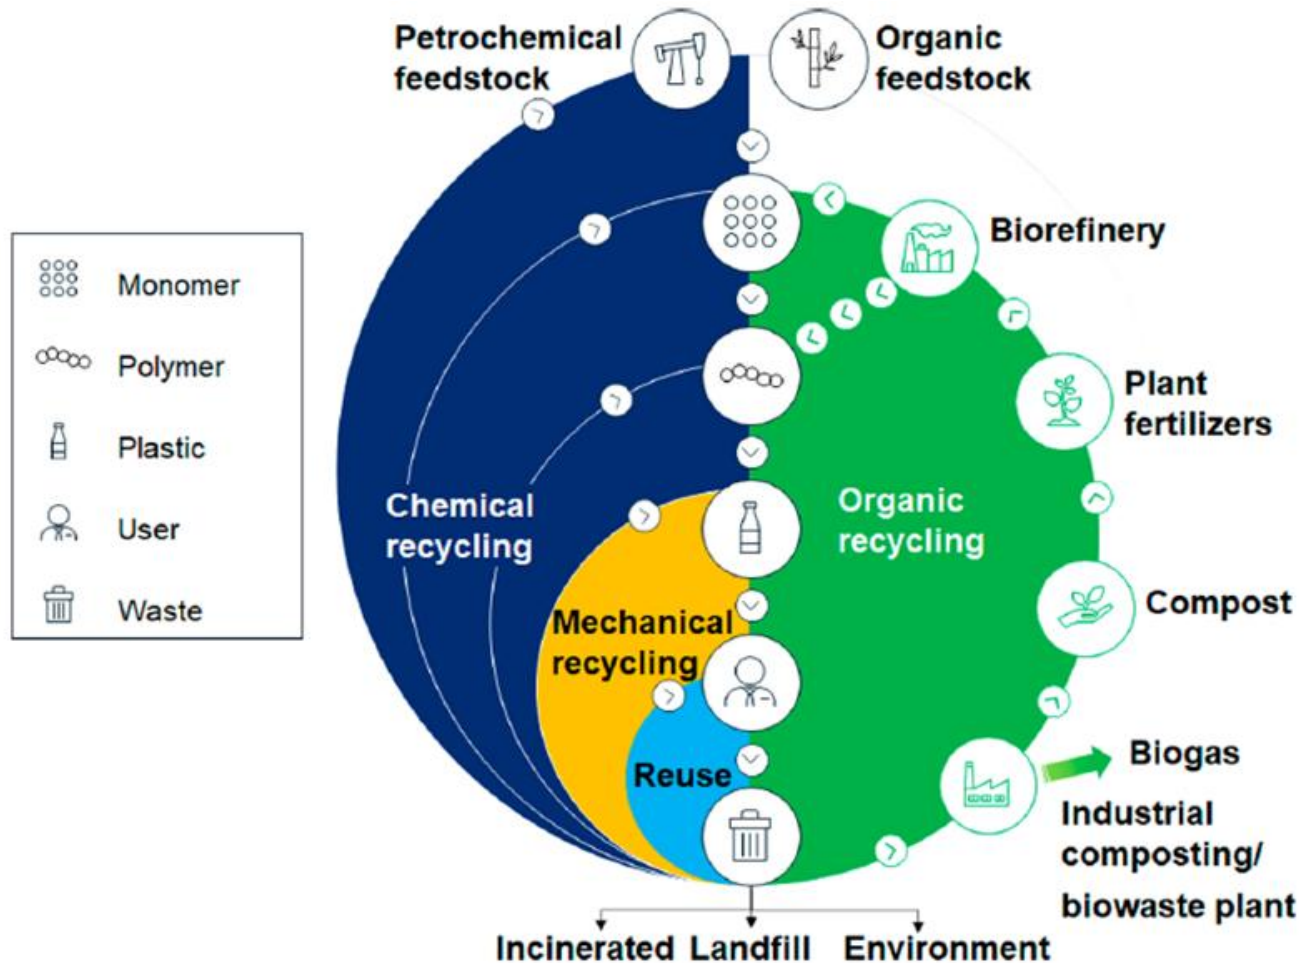


Moving from the **linear end-of-life** to the **circular end-of-life**.

Multimaterials

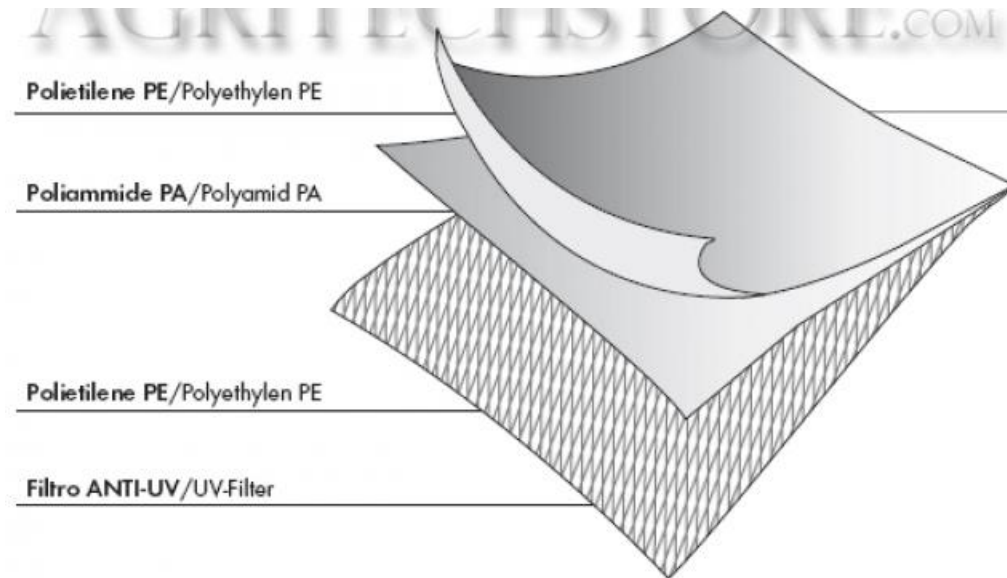


Use of oil

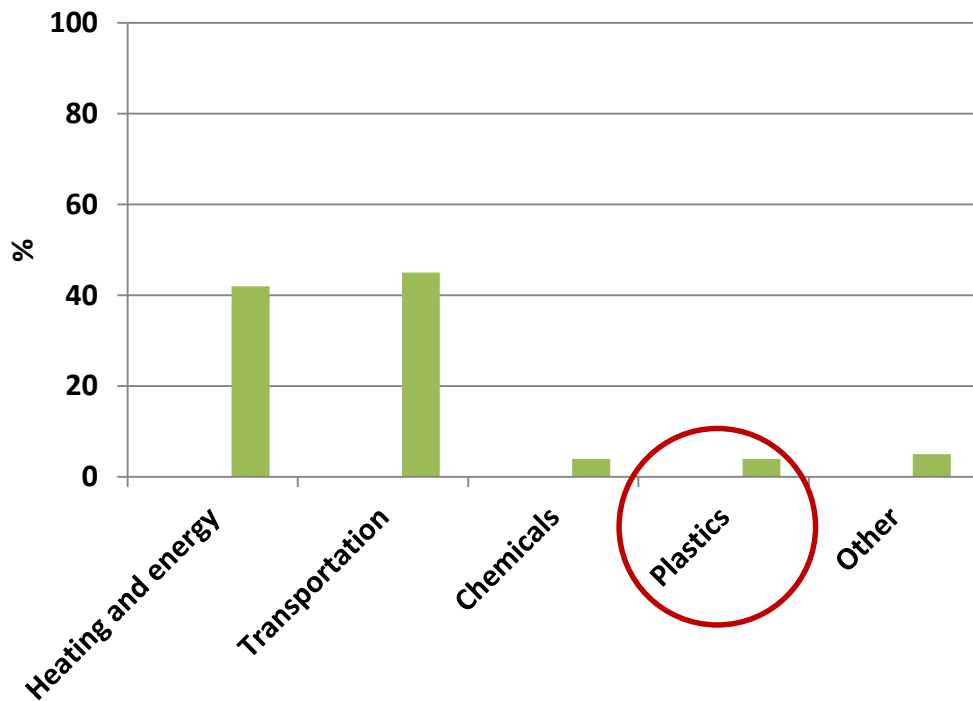

Kind of polyolefins

	LLDPE	LDPE	HDPE	UHMWPE	iPP
Density (g cm ⁻³)	0.90-0.94	0.91-0.94	0.94	0.930-0.935	0.88-0.92
Melting point (°C)	100-125	98-115	125-132	130-136	160-166
Cristallinity (%)	22-55	30-54	55-77	39-75	30-60

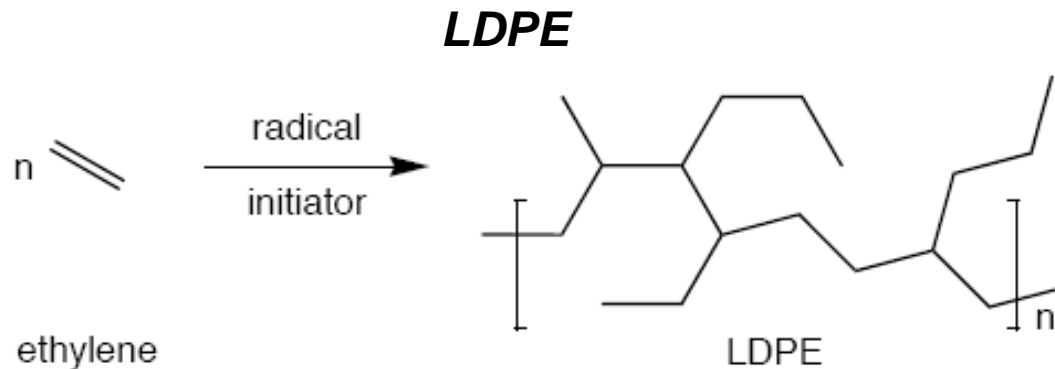


- LDPE: Low density polyethylene
- Highly branched material
- Properties and usage:
 - Stretchable before tearing
 - Used for flexible plastic bags
 - Recycled material: trash bags, grocery sacks



LDPE

Global production of **polyolefins** (10⁶ ton)

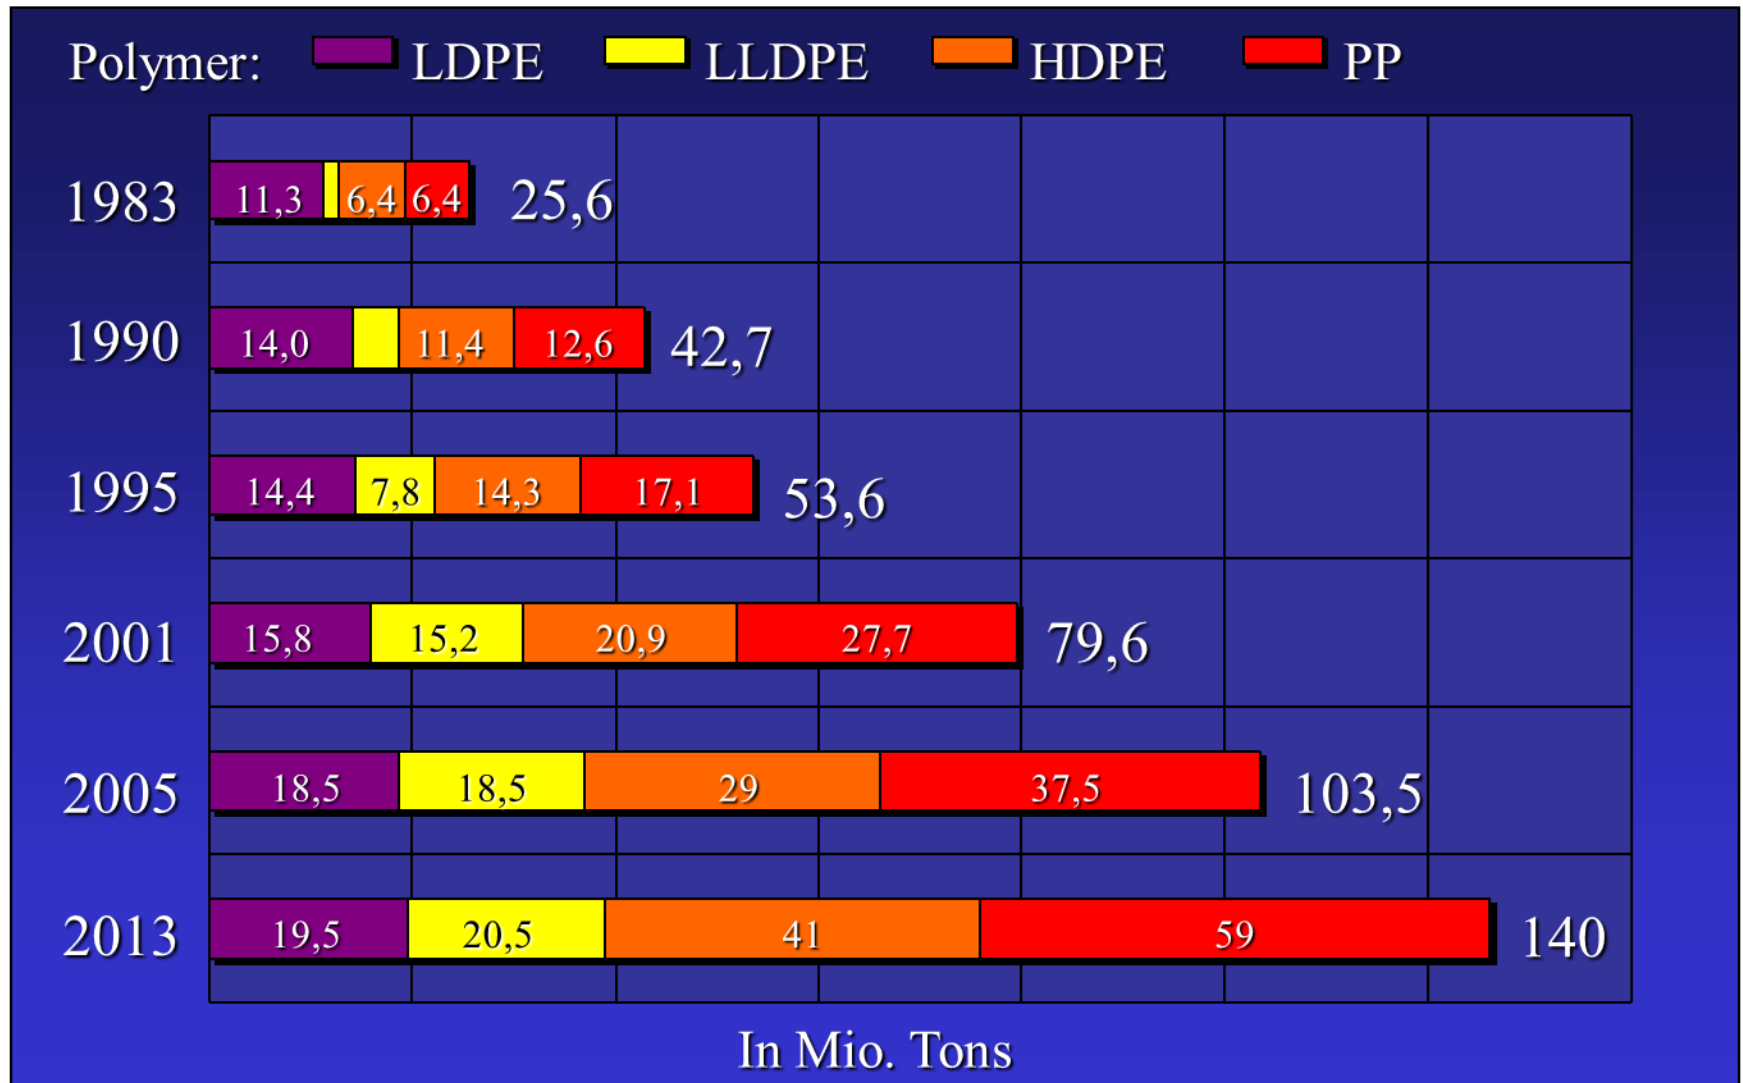

W. Kaminsky, *personal communication*.

Worldwide production of polyolefins in 2005 (10^6 ton/year)




Total production in 2010: $120 \cdot 10^6$ ton.*

W. Kaminsky *Macromol. Chem. Phys.* **2008**, 209, 459.

* Barzan, C.; Gianolio, D.; Groppo, E.; Lamberti, C.; Monteil, V.; Quadrelli, E. A.; Bordiga, S. *Chem.-Eur. J.* **2013**, 19, 17277.

Methods of polymerization

Radical Anionic Cationic **Coordination-Insertion**

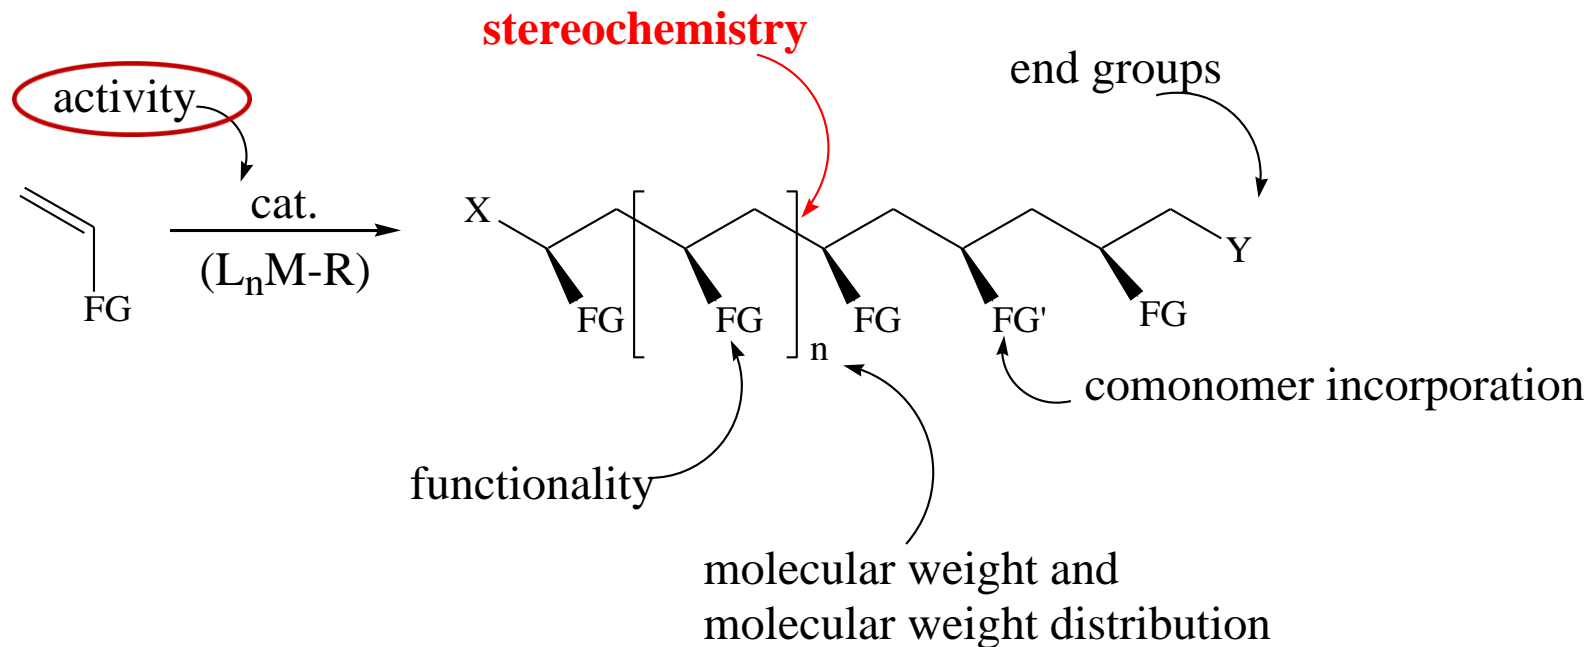


G. W. Coates et al. *Angew. Chem. Int. Ed.* **2002**, 41, 2236.

Rating effectiveness of a catalyst for polyolefin production

Rating	Very low	Low	Moderate	High	Very high
Activity (g P/mmol cat · h · bar)	< 1	10 - 1	100 - 10	1000 - 100	> 1000


Gibson, V. C. et al. *Angew. Chem. It. Ed.* **1999**, 38, 429.

Coordination – Insertion Polymerization (CIP)

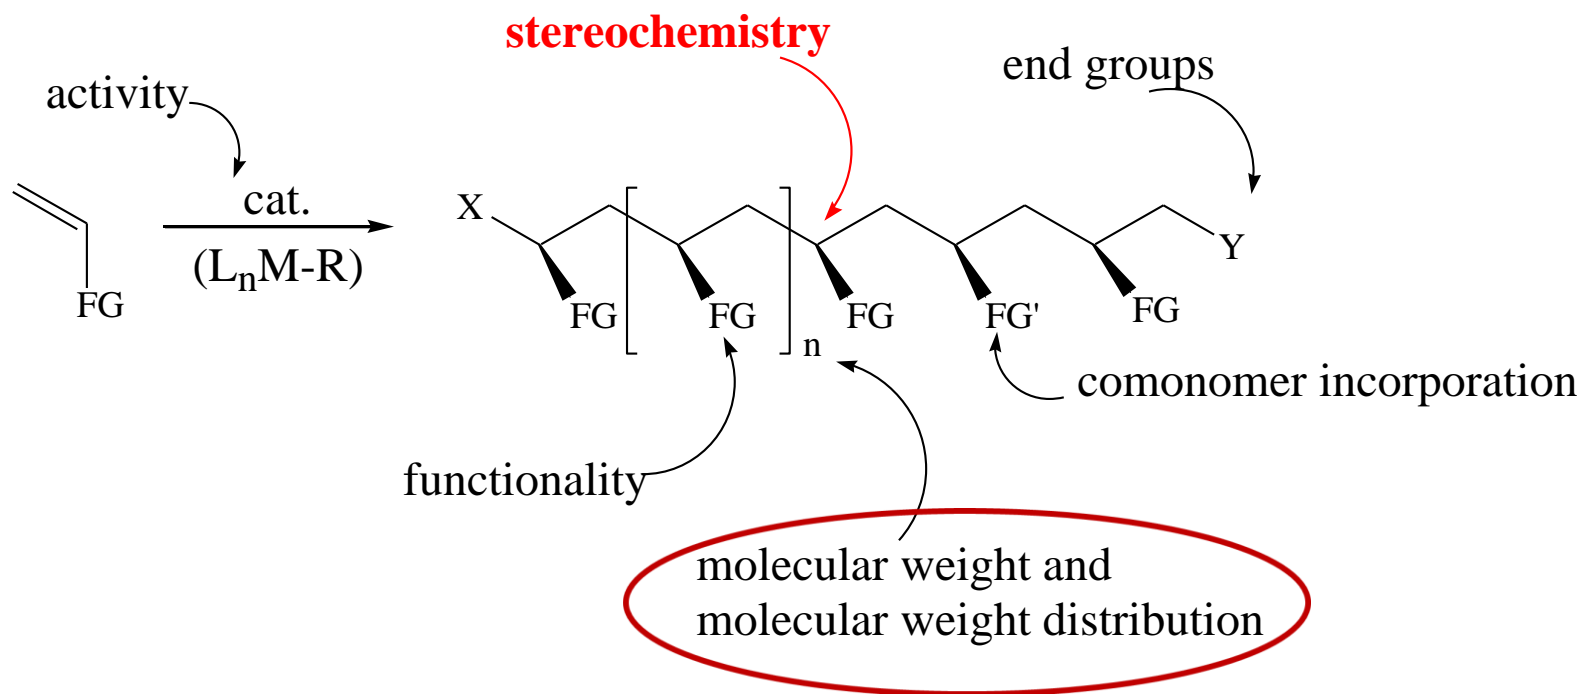

G. W. Coates et al. *Angew. Chem. Int. Ed.* **2002**, 41, 2236.

Molecular Weight and Molecular Weight distribution

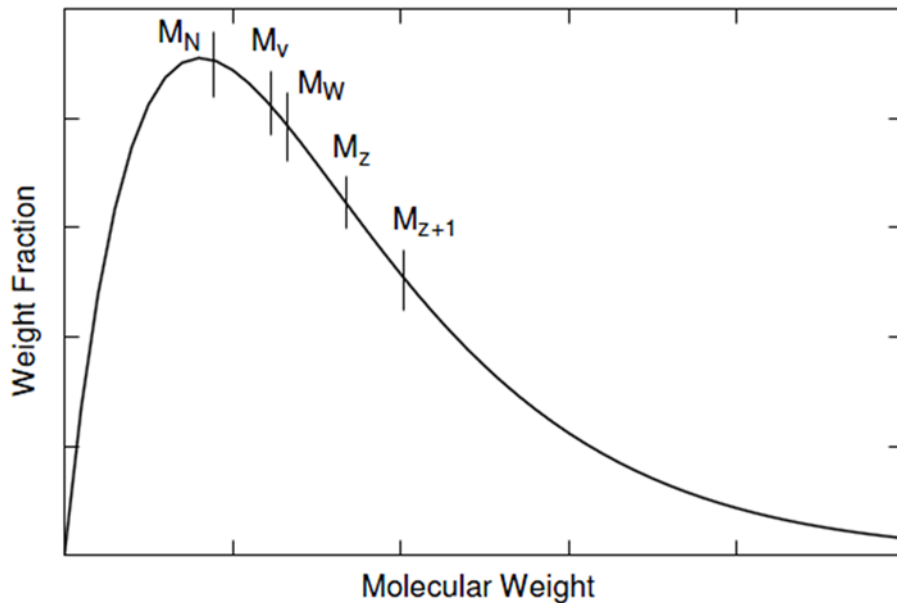


$$\langle M_n \rangle = \frac{\sum_{i=1}^{\infty} N_i M_i}{\sum_{i=1}^{\infty} N_i}$$

$$\langle M_w \rangle = \frac{\sum_{i=1}^{\infty} N_i M_i^2}{\sum_{i=1}^{\infty} N_i M_i}$$

- In a polydisperse polymer, $M_w \geq M_n$.
- The polydispersity and breadth of plot have bearing on the mechanism of polymerization and the properties of the resulting polymer.

The polydispersity index

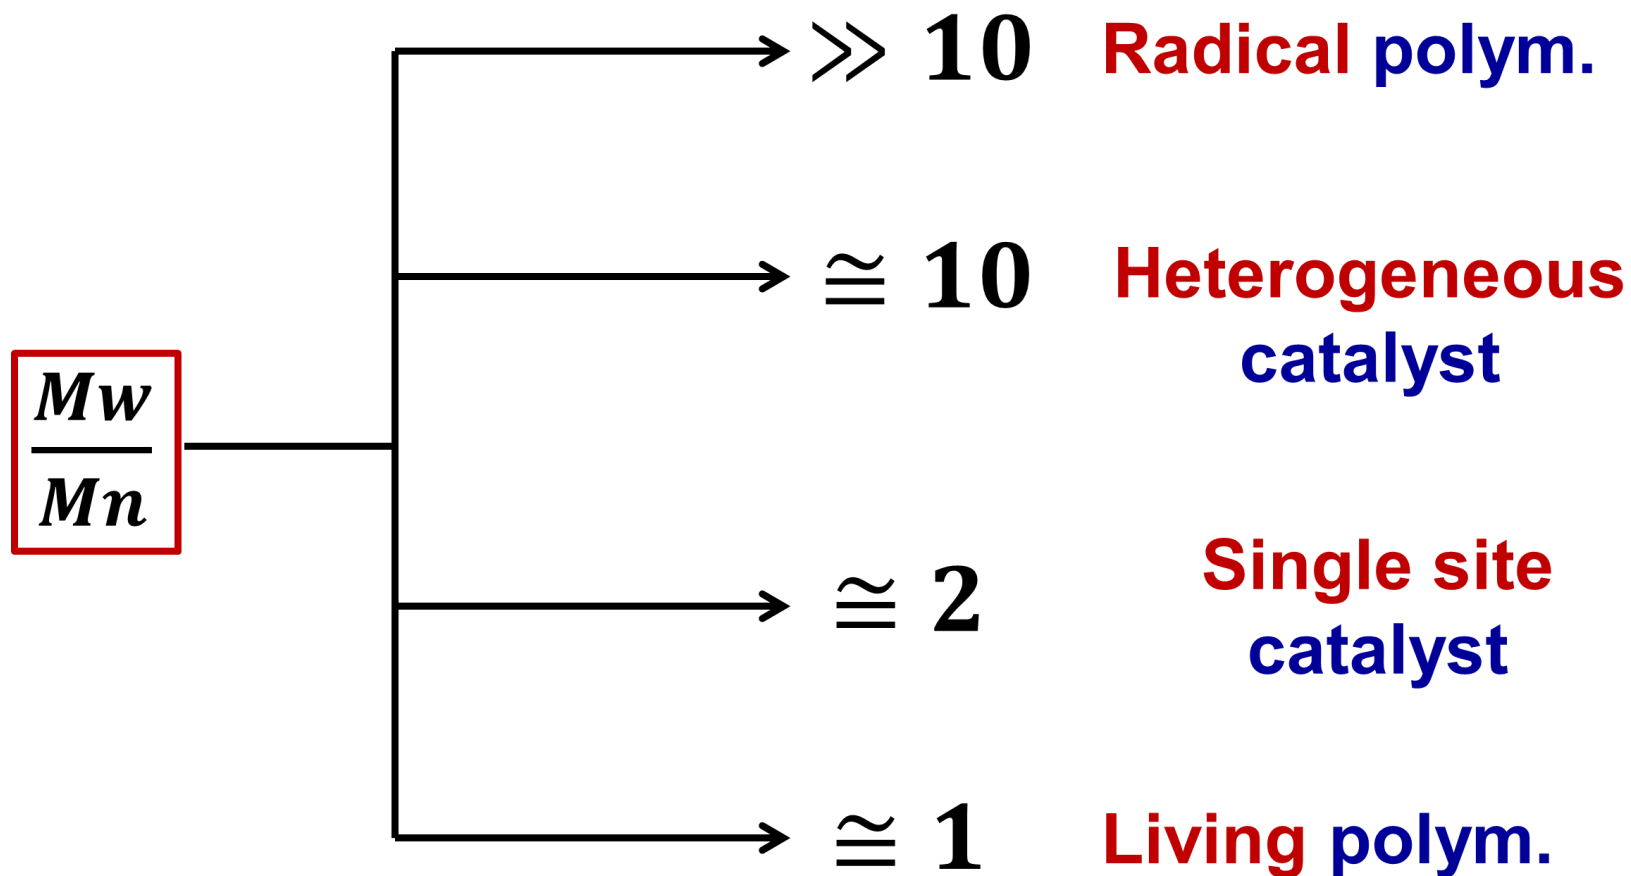

CIP Mechanism: the fundamental steps

Initiation step

k_i

M'
precatalyst

monomer

M

active
catalyst

$M \cdot ins$

polymer

n monomer

$M \cdot GPC$

$M \cdot mon$


Termination step

k_t

Propagation step

k_p

Molecular weight $\propto \frac{k_p}{k_t}$

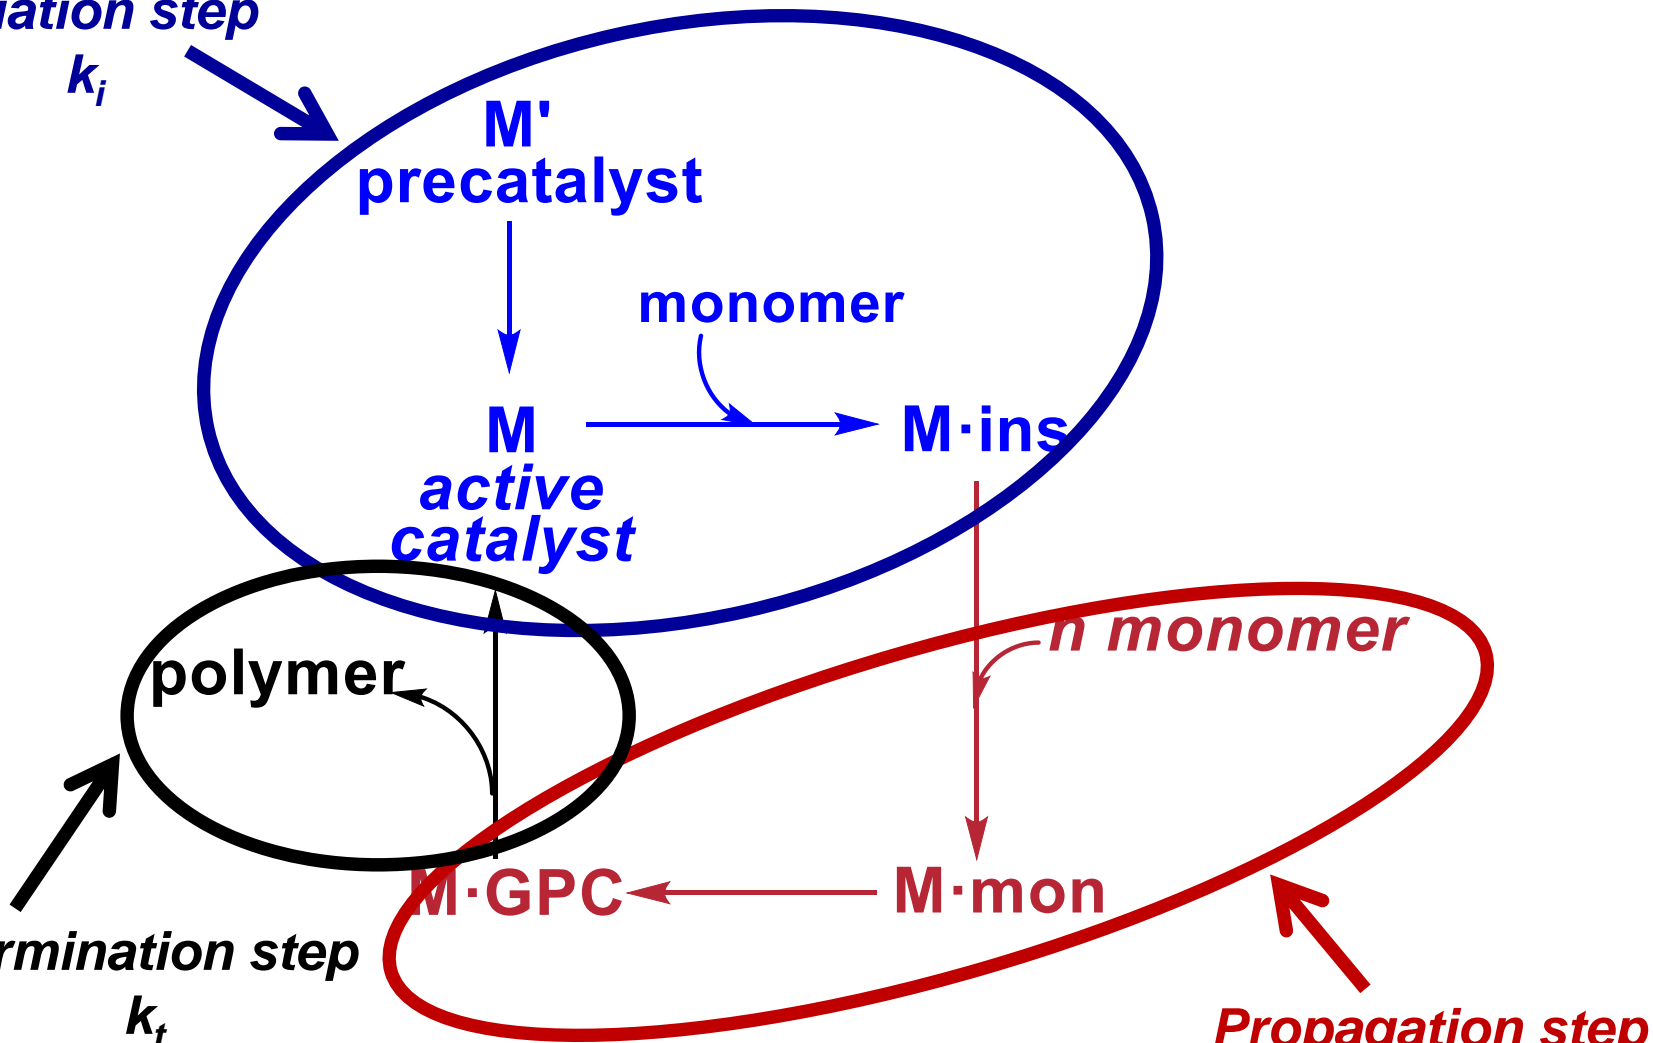

Polymerization Mechanism

Initiation step

k_i

- ❖ active species formation;
- ❖ reaction with the first monomer units;

Propagation step

k_p


- ❖ growth of polymer chain on the metal centre;

Termination step

k_t

- ❖ stop of the growth of the polymer chain;
- ❖ the active species is formed again.

Living polymerization: A special case

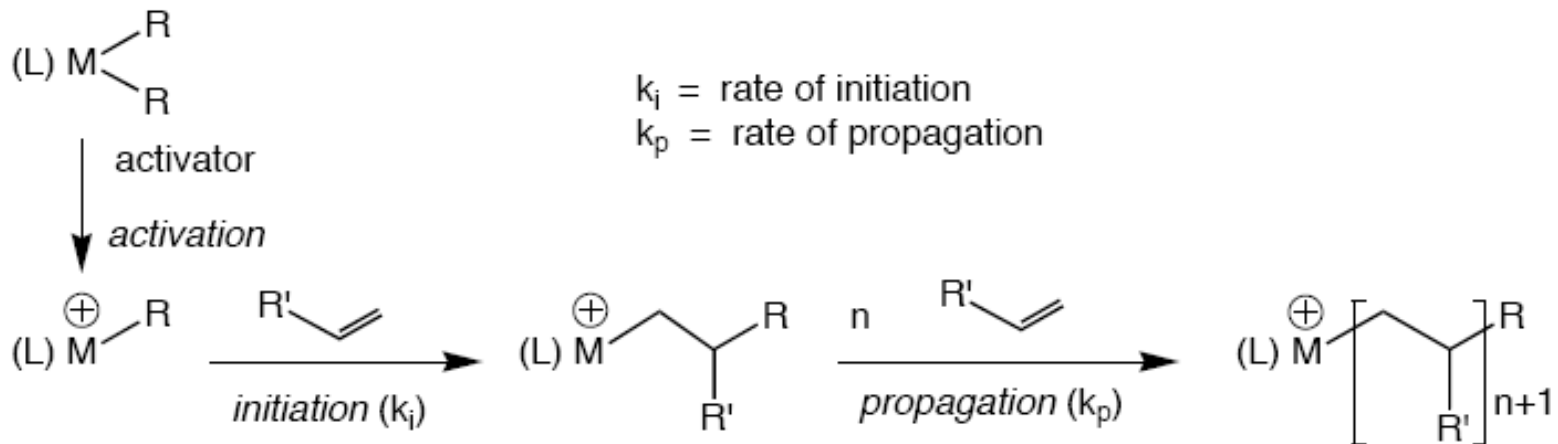


- Initiator and intermediates are stable under reaction conditions;
- There is **no chain termination**;
- **$k_i \geq k_p$** : this means that the rate of initiation is greater than rate of propagation and that all the metal centers are initiated before propagation takes place;
- Polymers with **narrow molecular weight distributions** are obtained.

Examples of analytical techniques applied for polymer characterization






Gel Permeation Chromatography

Size Exclusion Chromatography

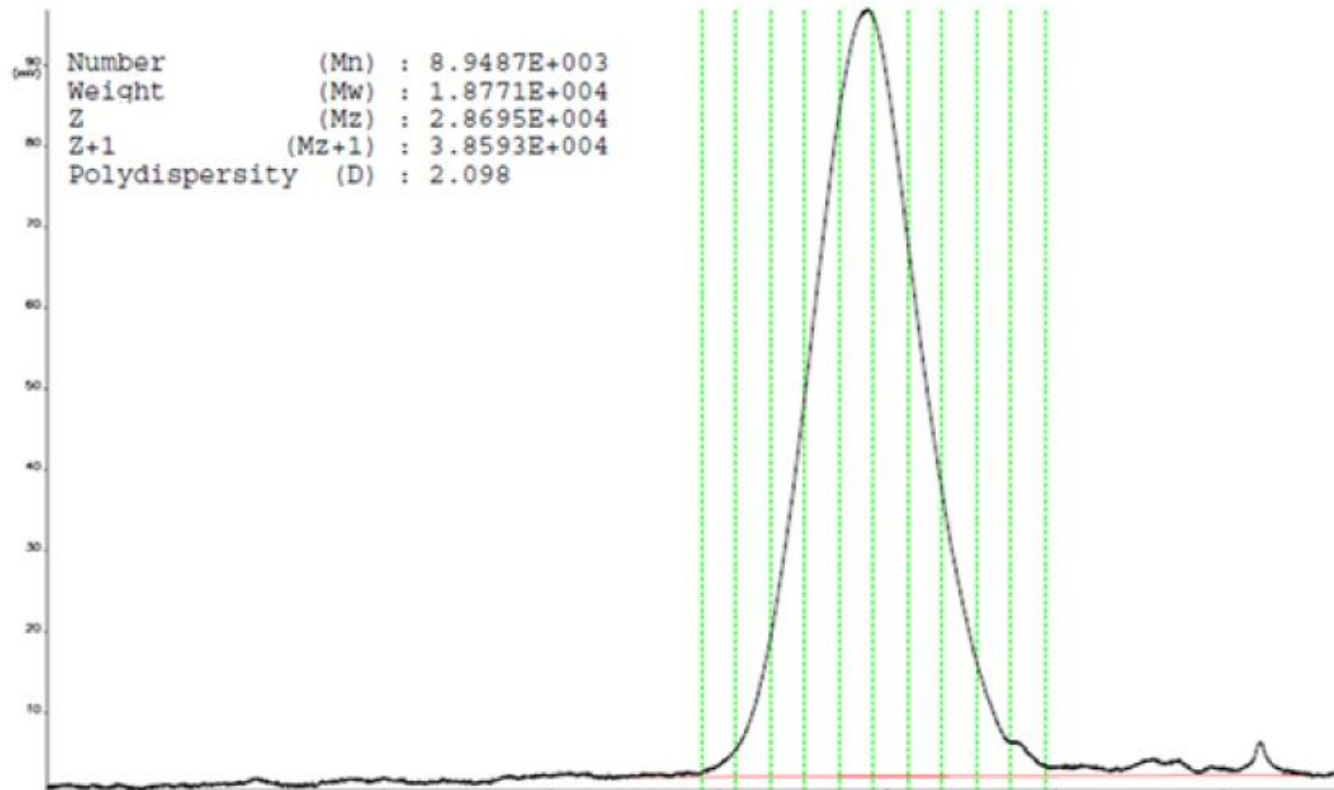

Examples of analytical techniques applied for polymer characterization

MALDI-TOF

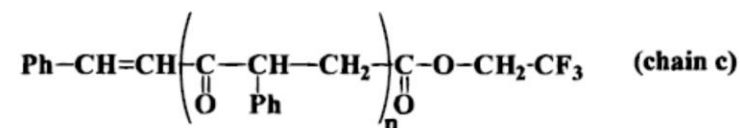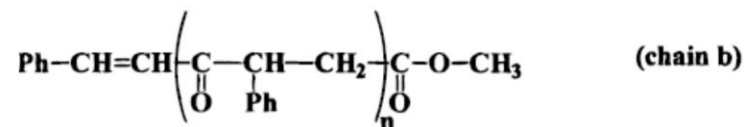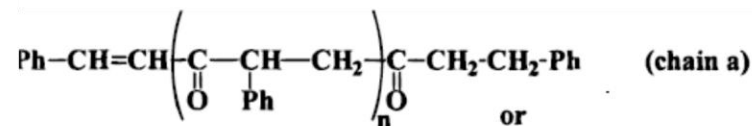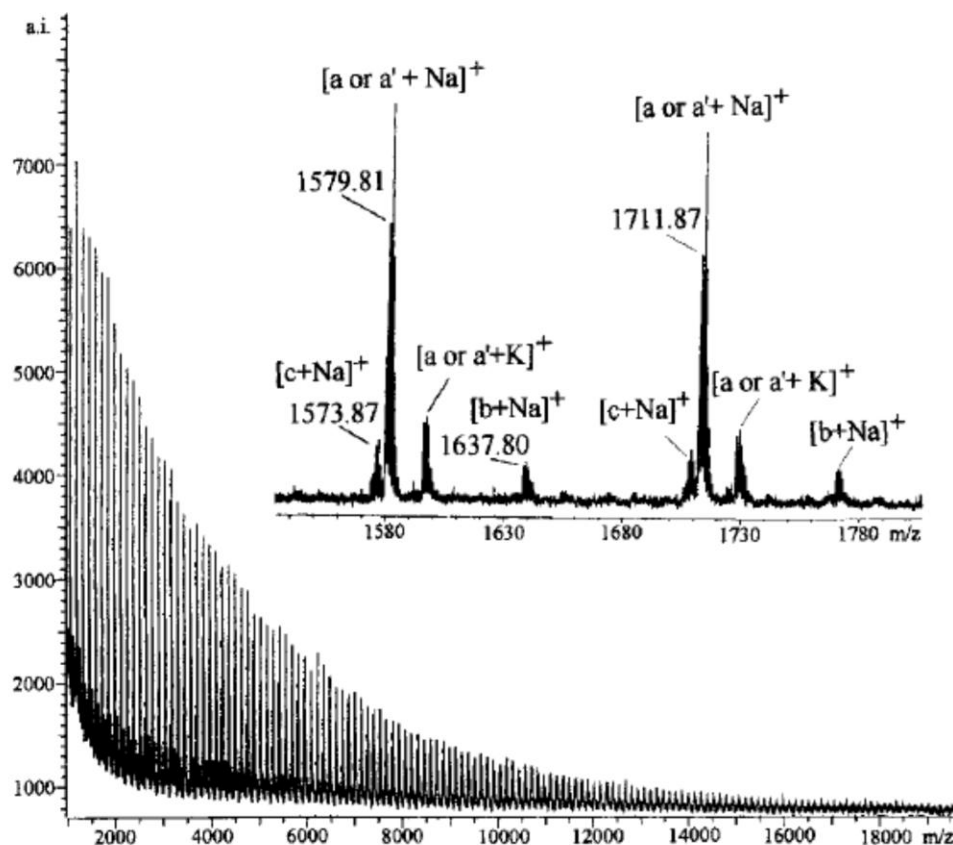

Milani, B. et al. *Organometallics* **2000**, *19*, 3435.

Examples of analytical techniques applied for polymer characterization



NMR Spectroscopy in solution allows to characterize macromolecules:

- ✓ **microstructure**: e.g. linear or branched chains;
- ✓ **regiochemistry**: head to tail, tail to tail, head to head enchainments;
- ✓ **stereochemistry**: different microtacticity;
- ✓ **end groups**: to gain information about initiation and termination steps;
- ✓ **content of comonomers**;
- ✓ **comonomer distribution**: random, block, alternate;
- ✓ **comonomer position**: into the main chain; in the branches.

Coordination – Insertion polymerization: The starting point.


1953. **POLYETHYLENE** is synthesized via catalysis for the first time under mild reaction conditions.
Ziegler.

1954. **STEREOREGULAR POLYPROPYLENE** is synthesized for the first time. The principle of **STEREOSPECIFIC POLYMERIZATION** is introduced.
Natta.

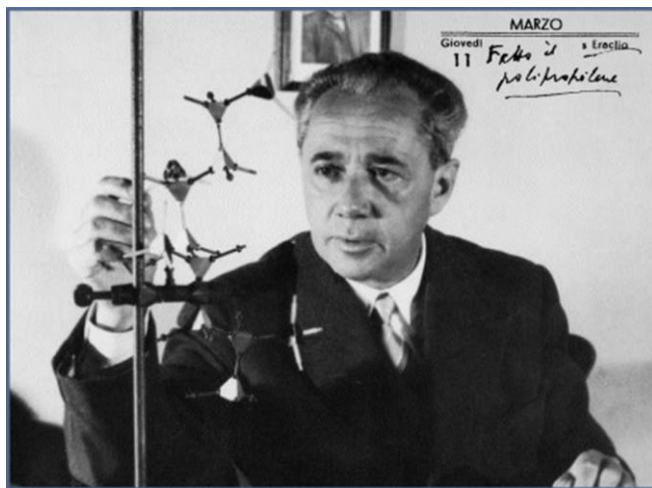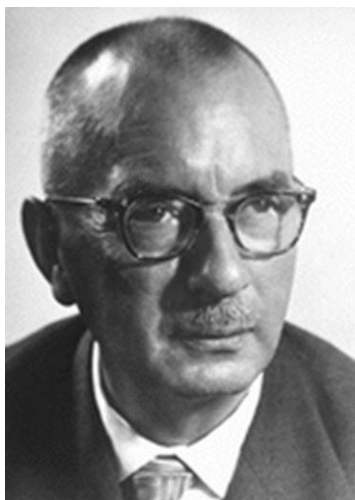

1963. Ziegler and Natta were awarded with the Nobel Prize for Chemistry

Synthesis of polyolefins

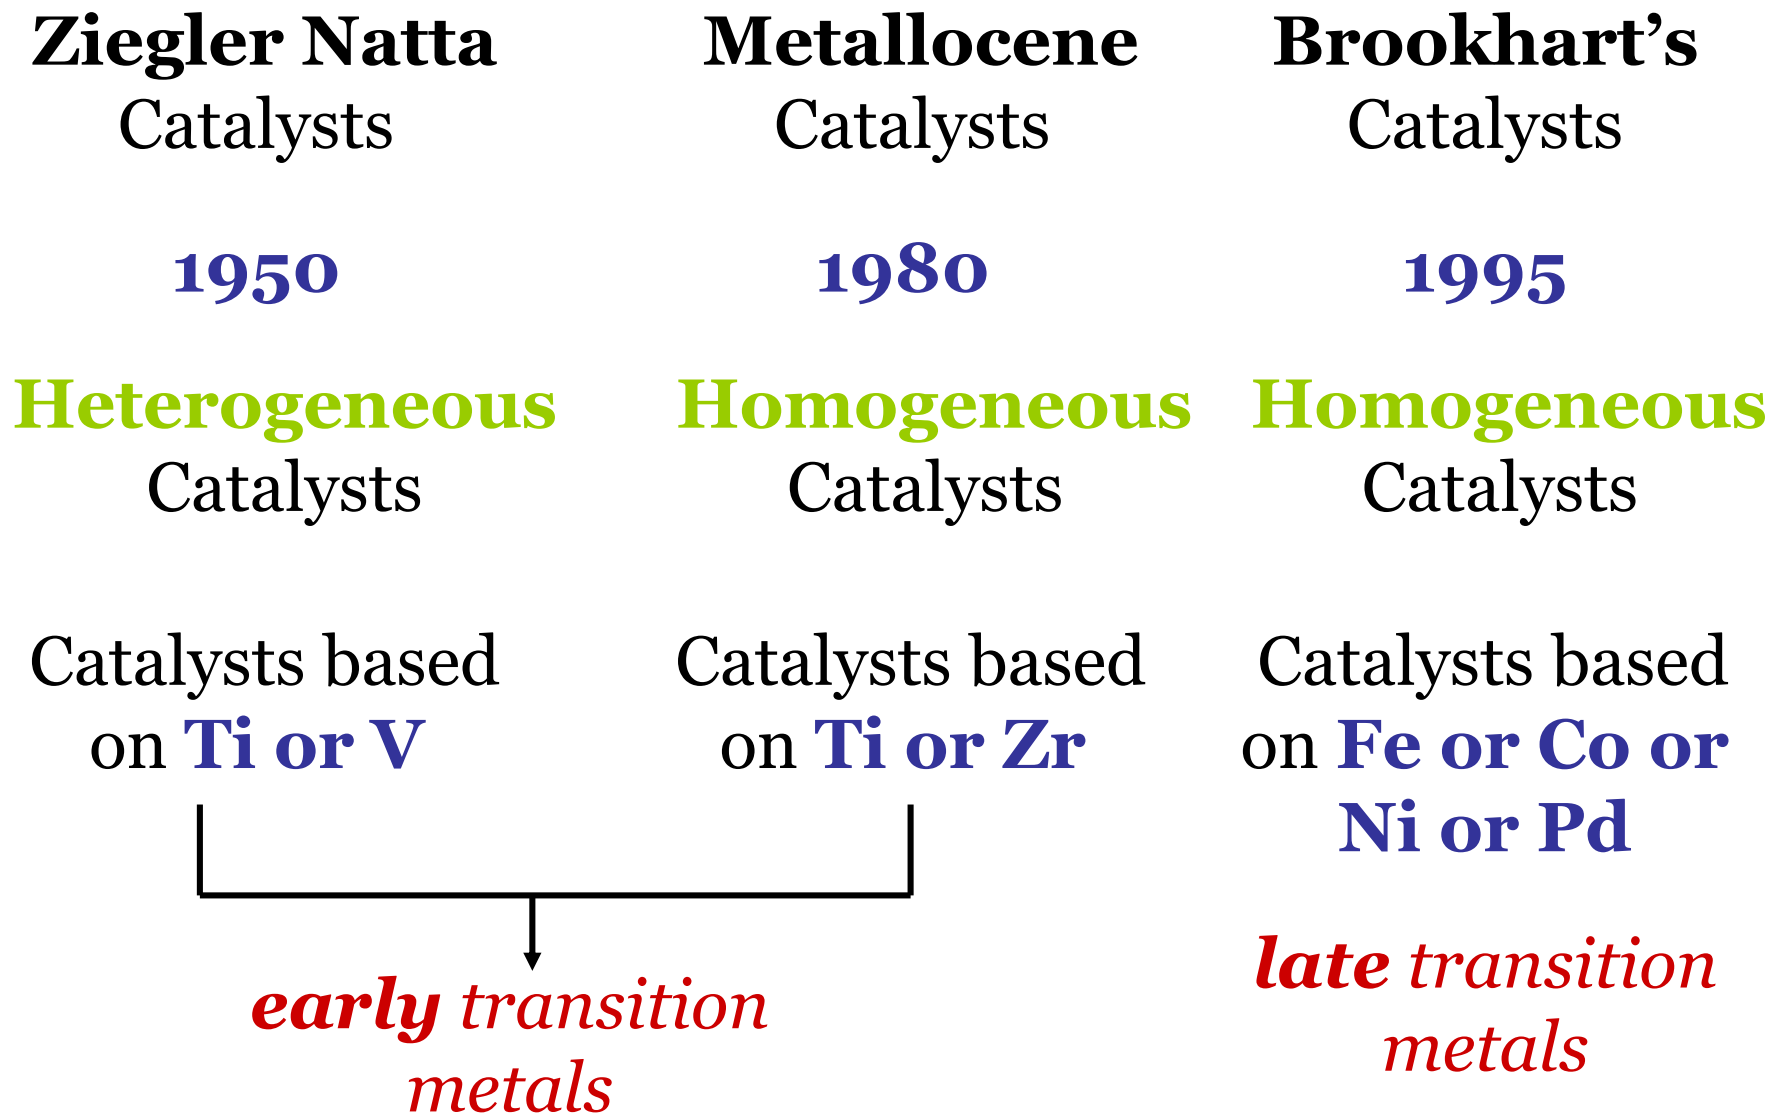

The Ziegler – Natta catalytic system

Heterogeneous Catalyst:




R = Et, *i*-But

$P_{\text{ethylene}} \approx 1 \text{ atm}$;

$T \leq 0^\circ\text{C}$

Highly exothermic process:
93.6 kJ/mol.

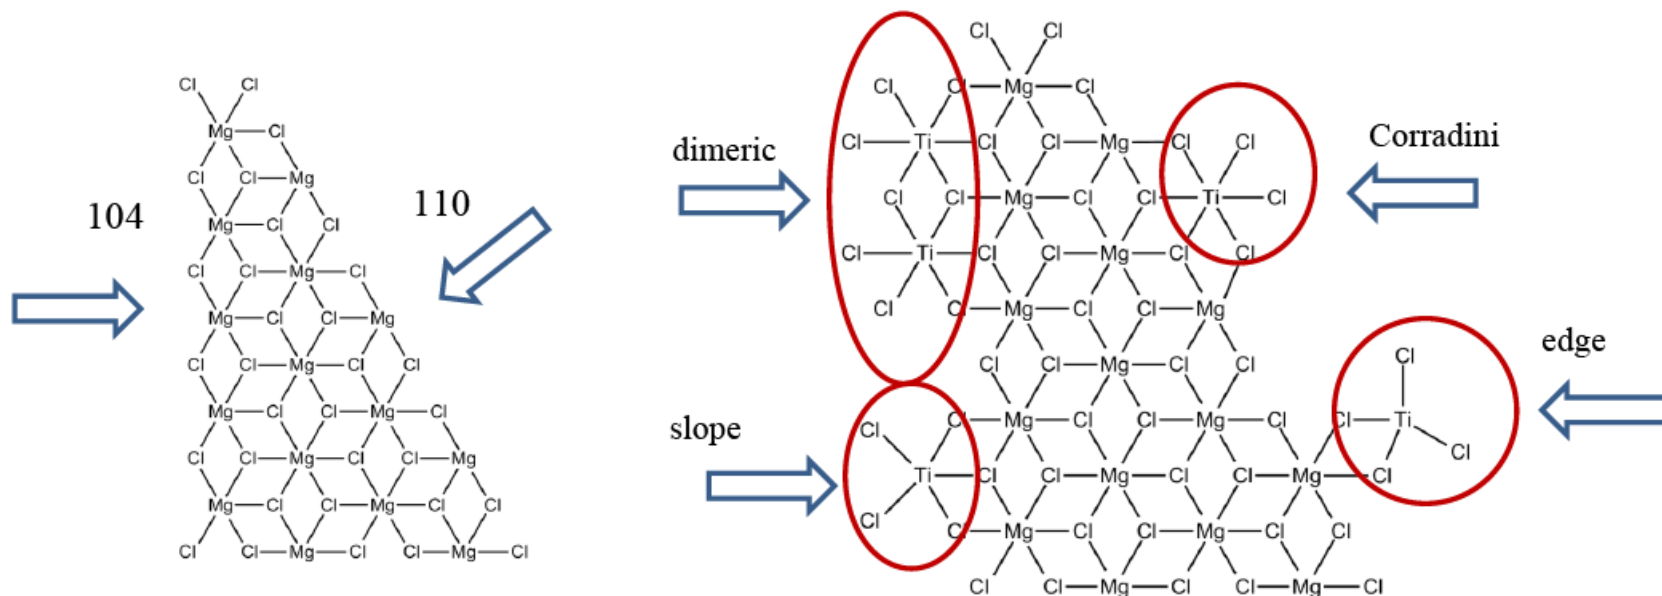


Polymerization Mechanism

Initiation step




Activation:

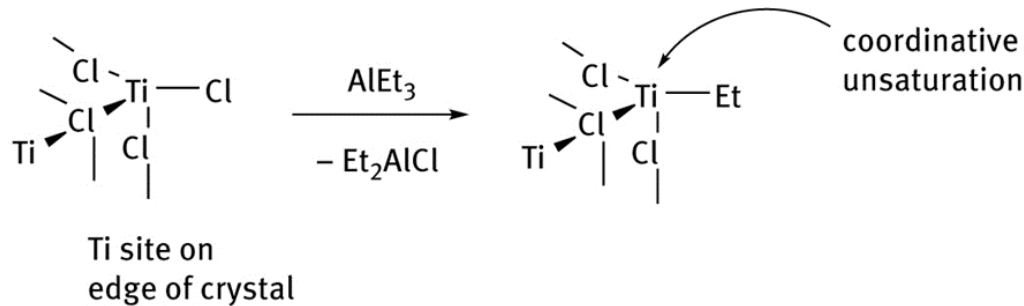

Polymerization Mechanism: (Cossee-Arleman)


Propagation step

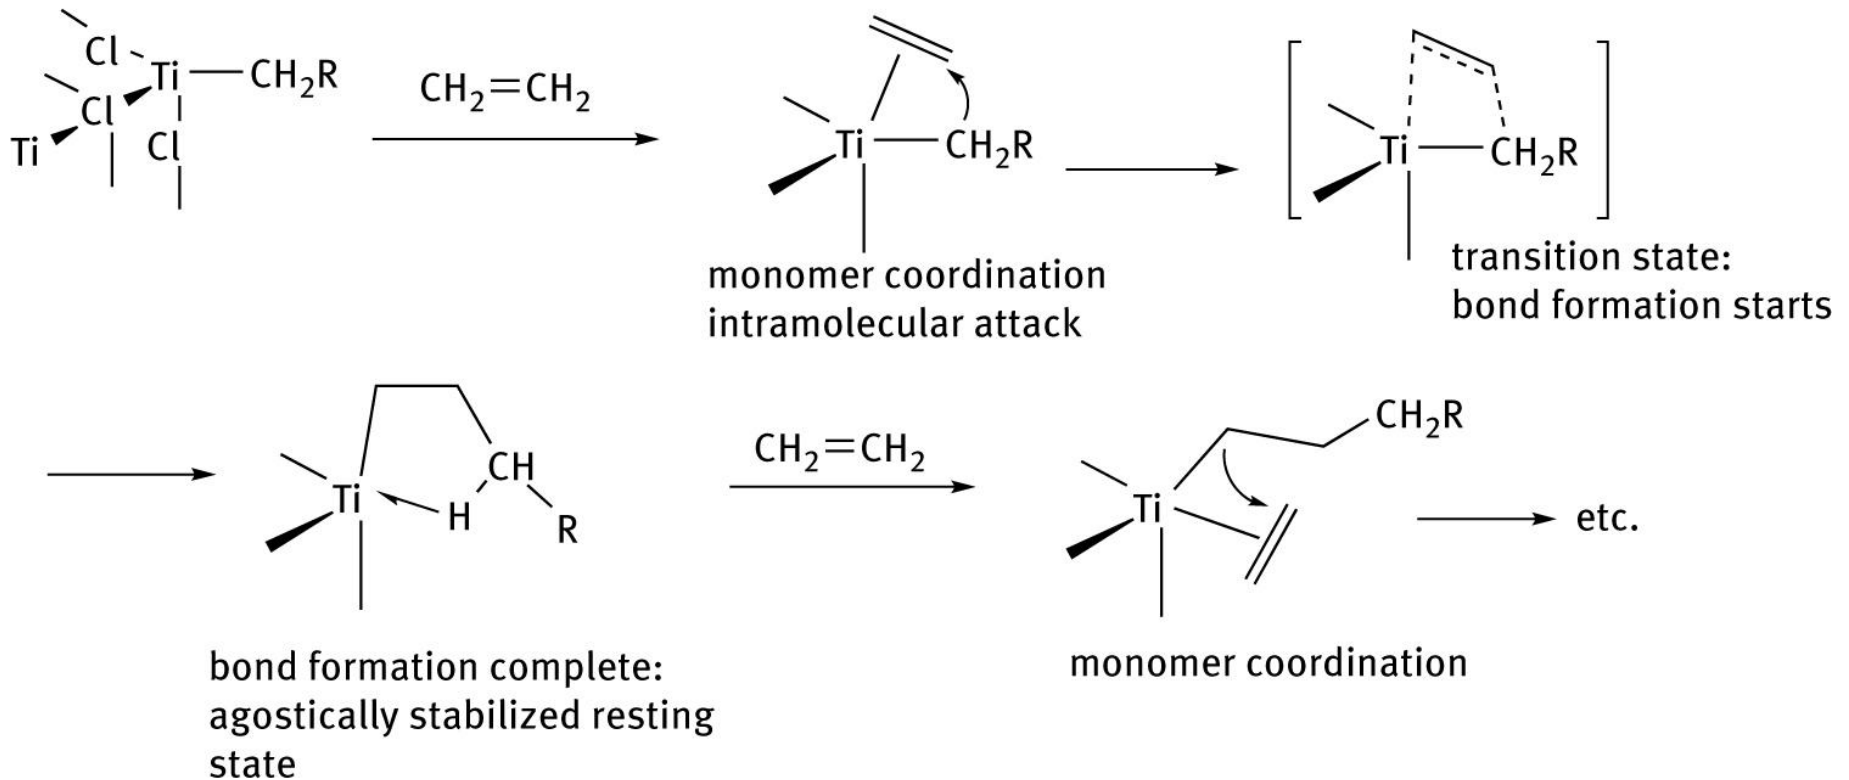

$$v = k_p[C^*][M]$$

Polymerization Mechanism

*Termination step:
chain transfer*

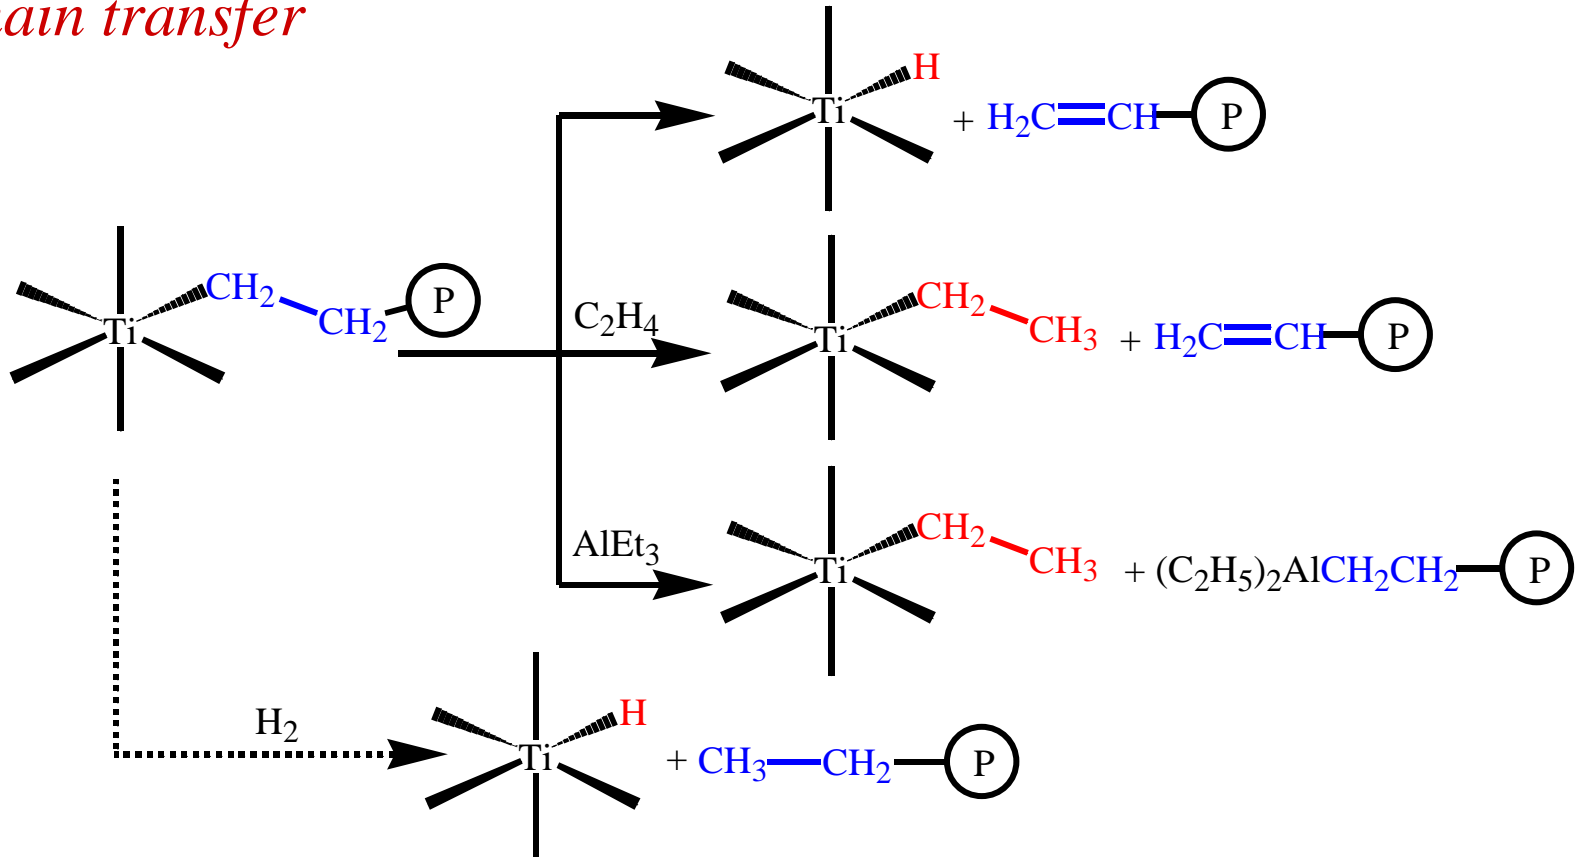

Limits of Ziegler Natta catalysts

- ❖ low amount of active sites: 1 – 20 % of Ti;
- ❖ 5 – 50 ppm of Cl_2 coming from the MgCl_2 support remain in the polymer, leading to potential corrosive phenomena during the polymer processing;
- ❖ it is possible to copolymerize with ethylene only a few terminal alkenes, and not in a random way;
- ❖ 3 – 4 % of oligomers remain in the polymer, which are released with time;
- ❖ it is difficult to have a control of the microstructure of the macromolecules.