STEREOCONTROLLED POLYMERIZATION


Asymmetric polymerization

Polymerization via asymmetric synthesis A *prochiral* monomer is polymerized to obtain a stereoregular polymer. During the polymerization process, the coordination of the incoming monomer on the catalyst takes place in a selective fashion through *only one enantiotopic face*.

Examples:

Polymerization of vinylic monomers, such as propylene, styrene.

Polymerization of conjugated 1,3-dienes.

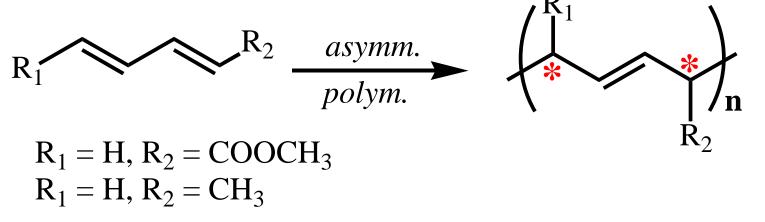



Asymmetric polymerization

Polymerization selective for the helic sense The chirality of the synthesized polymers is based on the *helic conformation*, that is right handed or left handed. The polymers are optically active.

Only one chain with a *preferential conformation* is synthesized.

Examples:

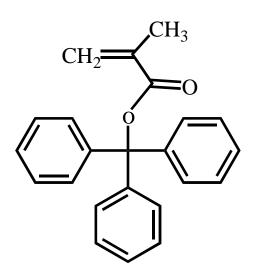

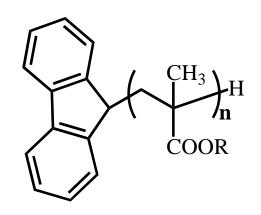


Asymmetric polymerization

Stereoelective polymerization

A *chiral racemic monomer* is used. Only *one enantiomer* of the chiral racemic monomer is preferentially polymerized to yield an optically active polymer.

It is a *kinetic optical resolution* of a racemic monomer.

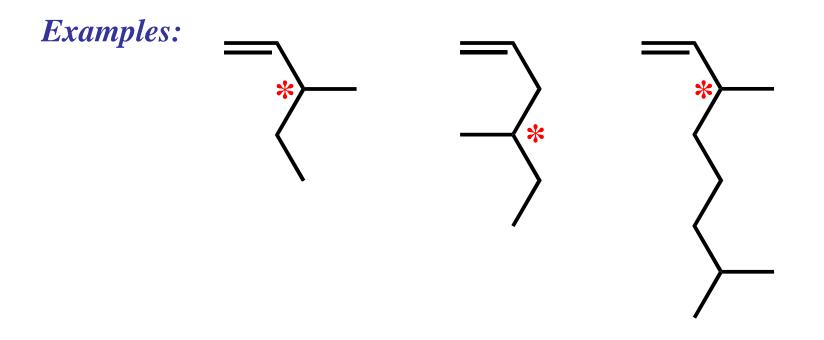

STEREOCONTROLLED POLYMERIZATION


Asymmetric polymerization

Polymerization via asymmetric synthesis A *prochiral* monomer is polymerized to obtain a stereoregular polymer. During the polymerization process, the coordination of the incoming monomer on the catalyst takes place in a selective fashion through *only one enantiotopic face*.


Examples:

Polymerization of vinylic monomers, such as propylene, styrene

Polymerization of conjugated 1,3-dienes.

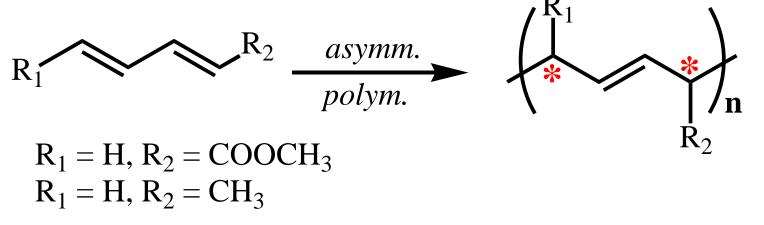


Polypropylene synthesis: The CRYPTOCHIRALITY phenomenon

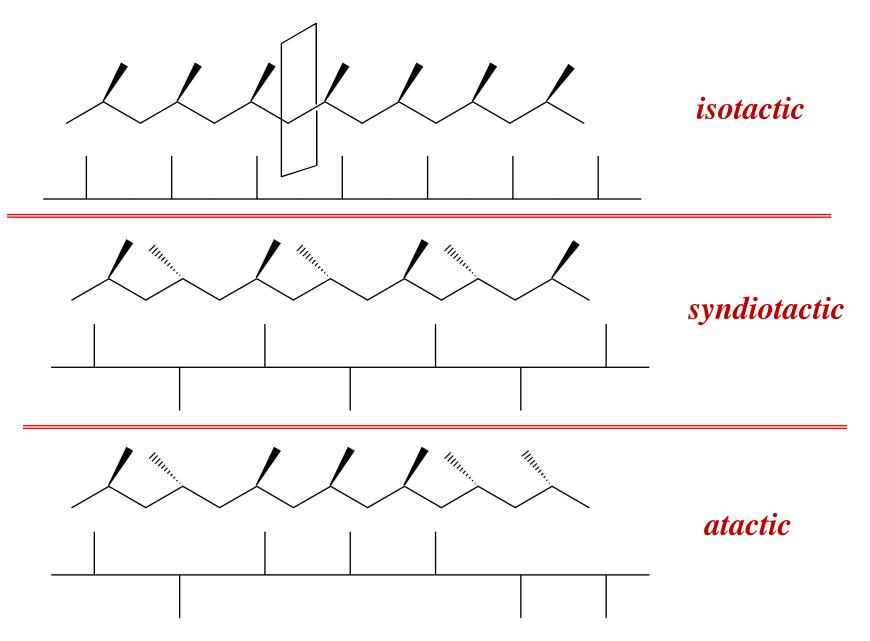


Polypropylene synthesis


Stereocontrolled polymerization: Control of stereochemistry via the nature of the ancillary ligands on the metal centre.



Multiple insertions of the same enantioface: *isotactic polymer*




Multiple insertions of the alternating enantiofaces: *syndiotactic polymer*




Random enantioface insertions: *atactic polymer*

Tacticity

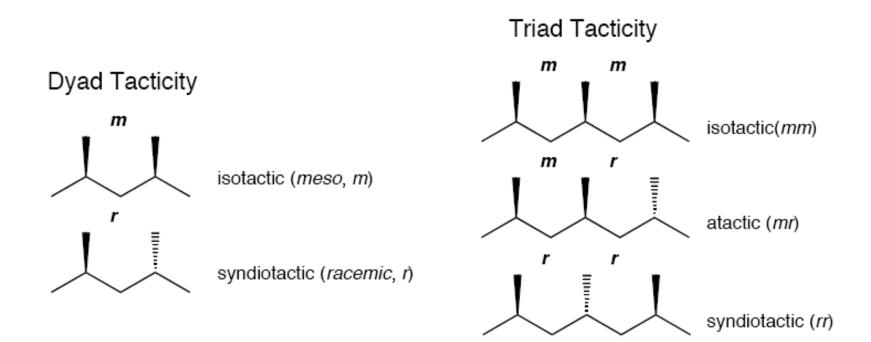


Tacticity


- Isotactic and syndiotactic polymers are crystalline, atactic is amorphous;
- NMR spectroscopy is a powerful tool for studying polymer Stereochemistry.
 - Tacticity of polymer is determined by % m or r dyads e.g. Perfectly isotactic polypropylene has 100% m dyads

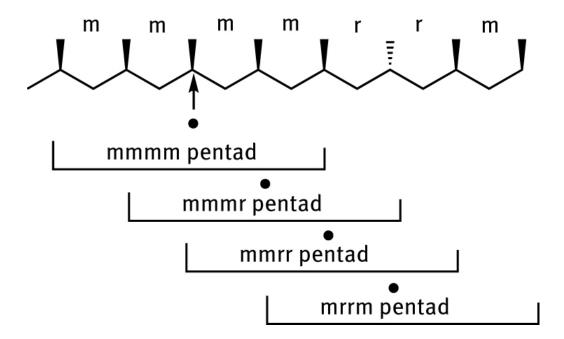

Microtacticity ¹³C NMR Spectra of polypropylene: methyl pentad region

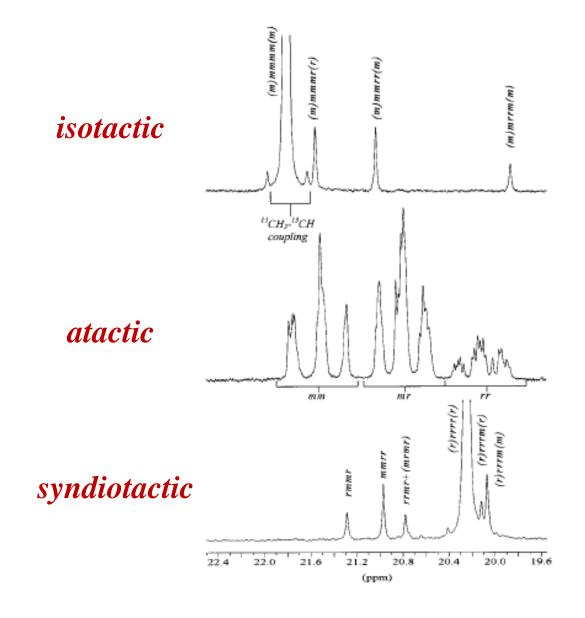

Regiochemistry

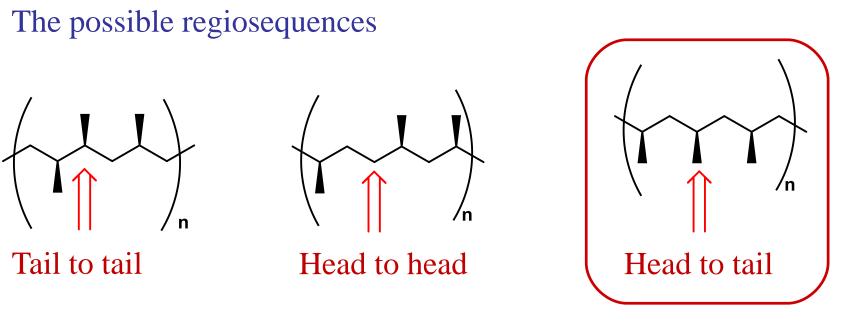


are originated by 1,2-Insertion or 2,1-Insertion

isolated regio-error

ENANTIOSELECTIVE CATALYSIS¹

Enantioselective synthesis of small molecules

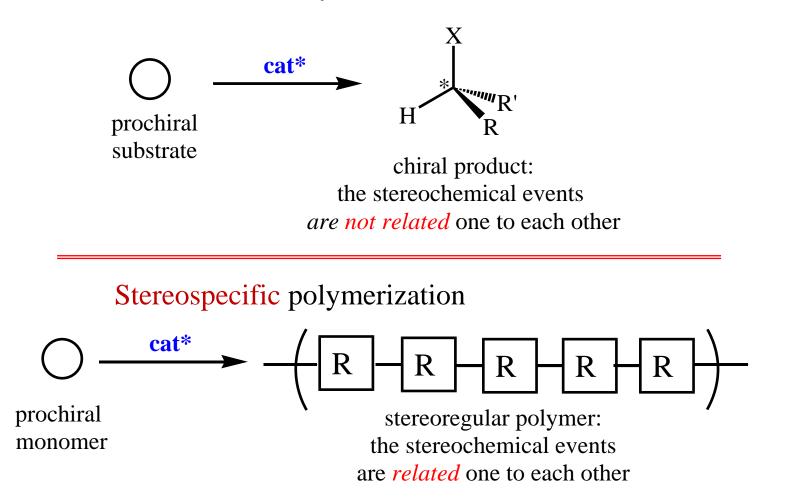


cat* = chiral coordination compound


¹G. W. Coates et al., Angew. Chem. Int. Ed. 2000, 39, 3626.

STEREOSPECIFIC Ziegler-Natta Catalysts

Synthesis of *isotactic* polypropylene

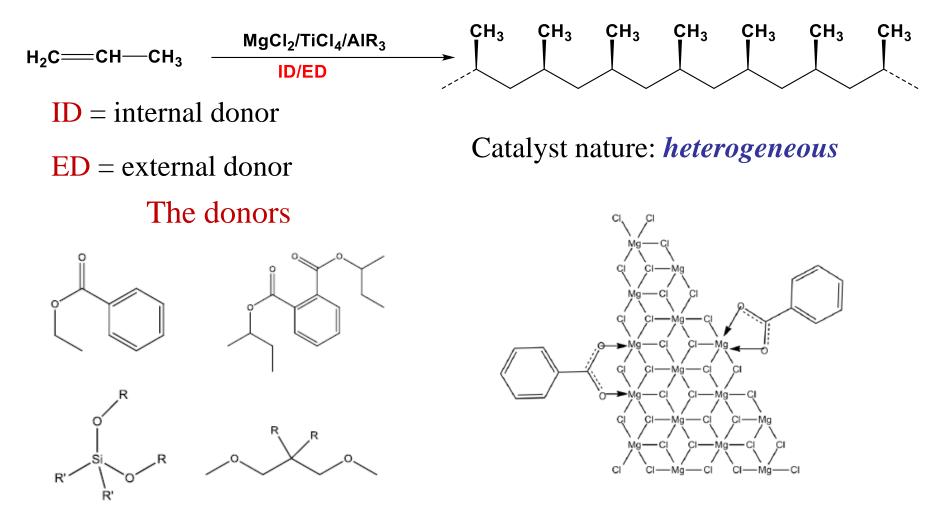


Z-N Catalyst Preparation The solid Catalyst Precursor

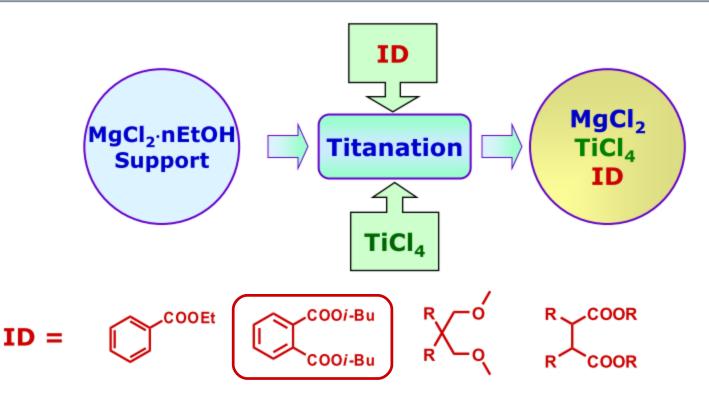

The Internal Donor is added (alone or in mixture) during the catalyst preparation, with the goal to:

- stabilize nascent MgCl₂ crystallites
- I influence the crystallite dimensions and thus the "working surface" connected with the productivity of the resulting catalyst
- control of the distribution of TiCl₄ on the possible MgCl₂ cuts

Z-N Catalyst Preparation Activation of the catalyst: ED structures

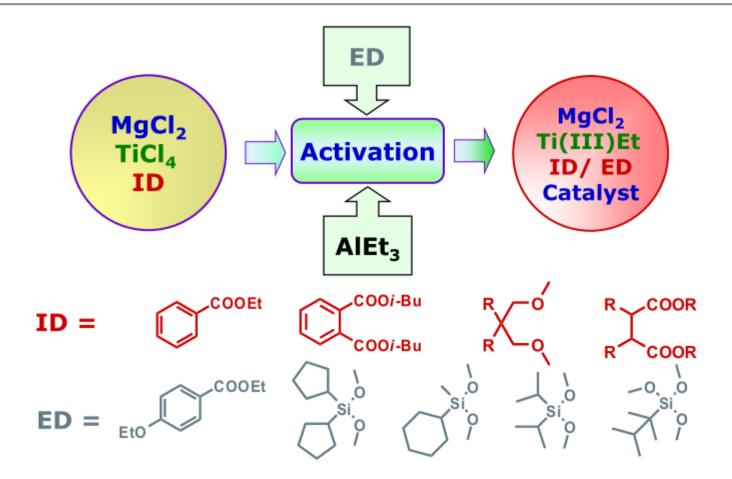

15000 kg PP/mol Ti MPa h of i-PP 97 -98 %

Morphology of supports and PP particle




Morphology of catalyst support: spherical.



Morphology of catalyst of PP particles.

STEREOSPECIFIC Ziegler-Natta Catalysts

Synthesis of *isotactic* polypropylene




Heterogeneous catalyst.

Stereochemistry of the insertion step: nature of the errors:




Errors of kind A are indicative for the chiral nature of the catalyst.

Enantiomorphic site control

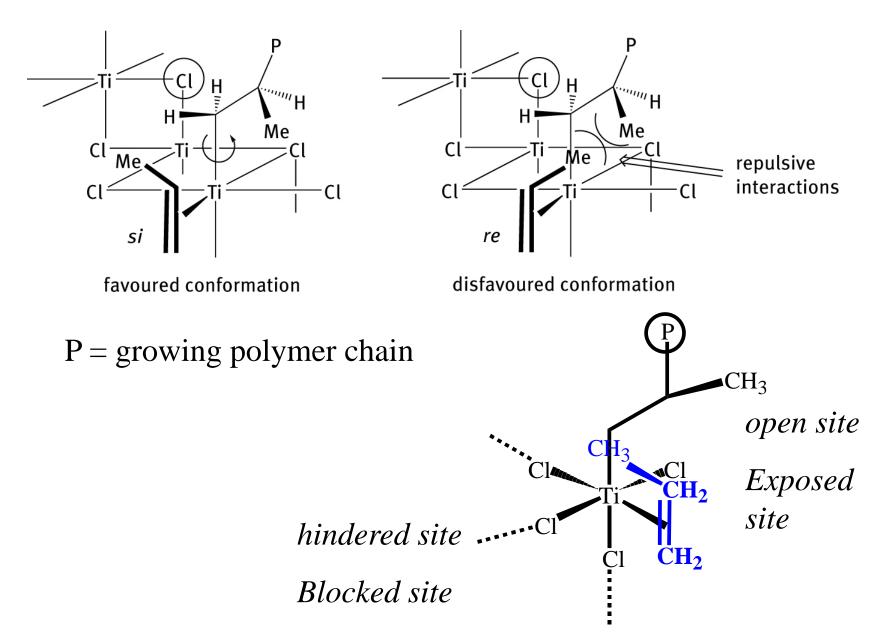

STEREOSPECIFIC Ziegler-Natta Catalysts

Synthesis of syndiotactic polypropylene



Catalyst nature: *homogeneous*

General aspects of stereospecific polymerization of propylene

Catalyst

Stereoregularity


Regioselectivity

Control of stereochemistry


 $MgCl_2/TiCl_4/AlR_3$ isotactic primary enantiomorfic site

VCl₄/C₆H₅OCH₃/Al(C₂H₅)₂Cl syndiotactic secondary chain end $L_nM-CH-CH_2-P$

Soluble catalysts

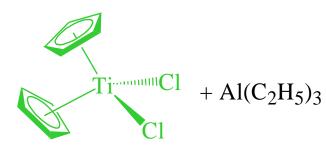


Low activity towards ethylene Inactivity towards propylene

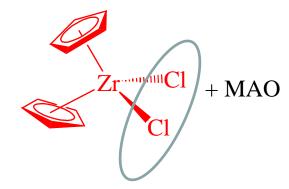

Very high activity towards ethylene


Good activity towards propylene

Metallocene catalysts

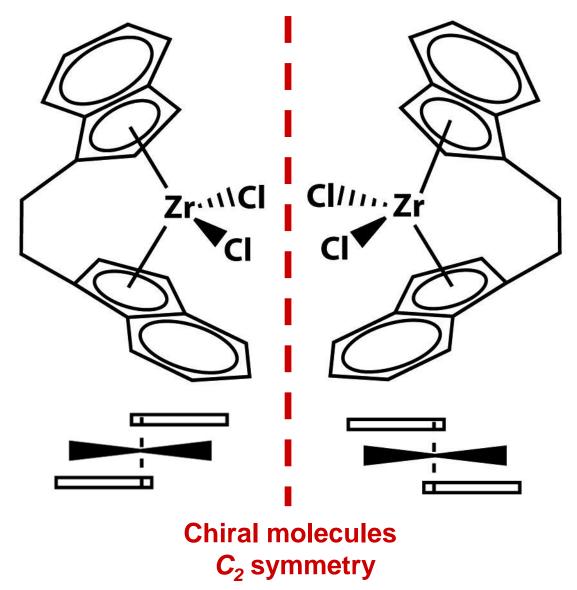

+ MAO leads to *isotactic* polypropylene

Metallocene catalysts

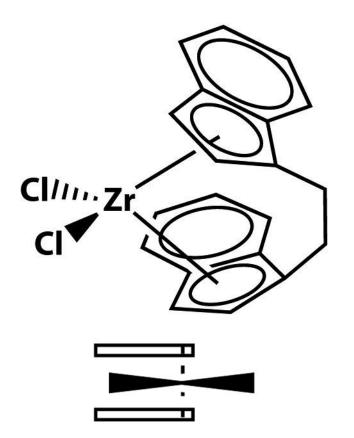


meso form of the molecule $C_{\rm s}$ symmetry

+ MAO leads to *atactic* polyproylene

ansa-zirconocenes catalysts: stereorigid of C_2 symmetry

The isotactic PP synthesized with metallocene catalysts differs from that obtained with catalysts based on Ti for:

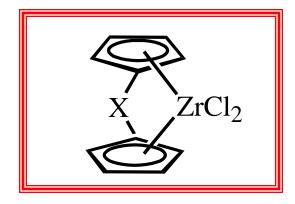


- Iower molecular weight;
- narrower molecular weight distribution;

the tacticity: from almost atactic to perfectly isotactic PP can be obtained;


not fully regioregular: insertions with secondary regiochemistry are also observed;


* random distribution of stereo- and regio-errors.


The evolution of metallocene catalysts¹: the root

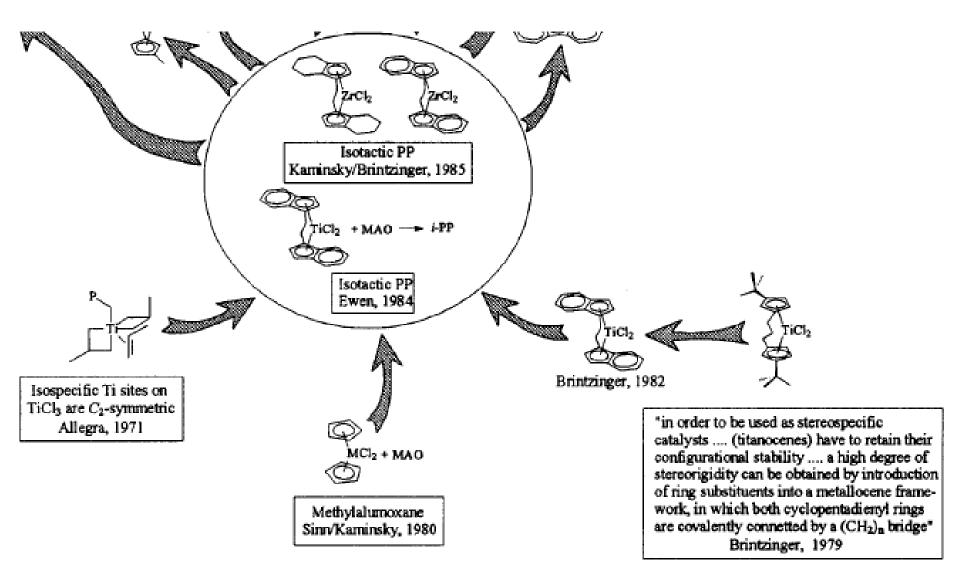

The evolution of metallocene catalysts: the tree

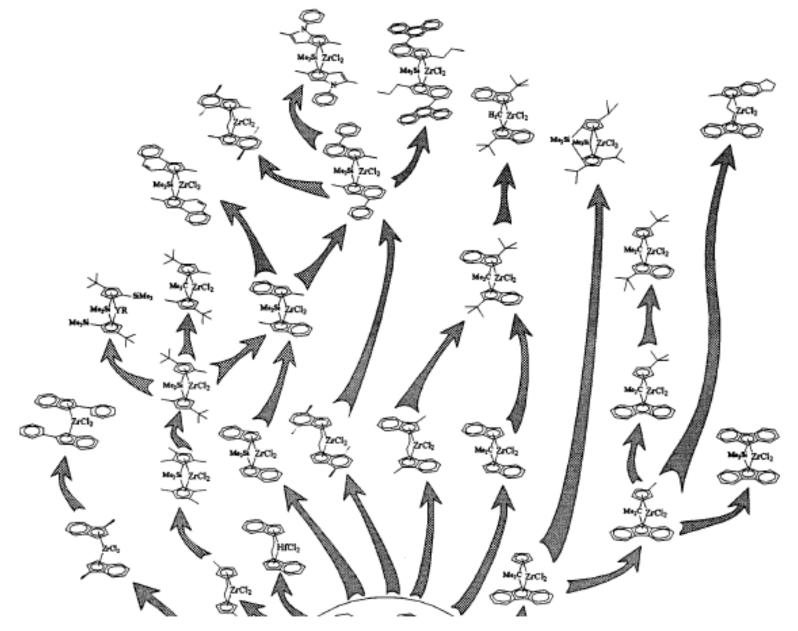


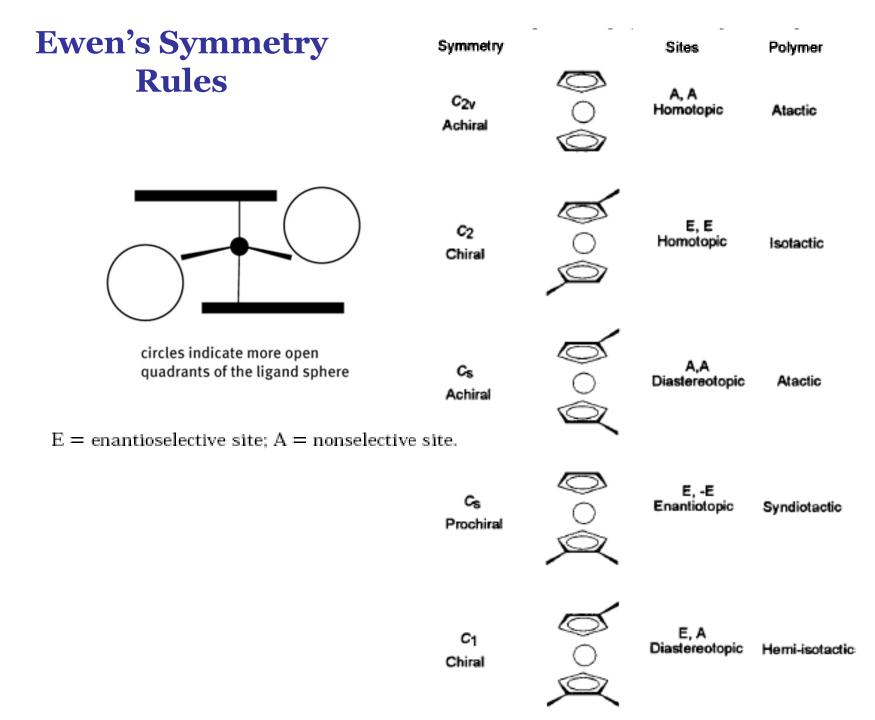

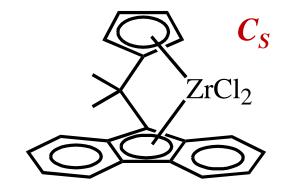


SYNDIOSPECIFIC Catalyst¹


ISOSPECIFIC Catalysts¹

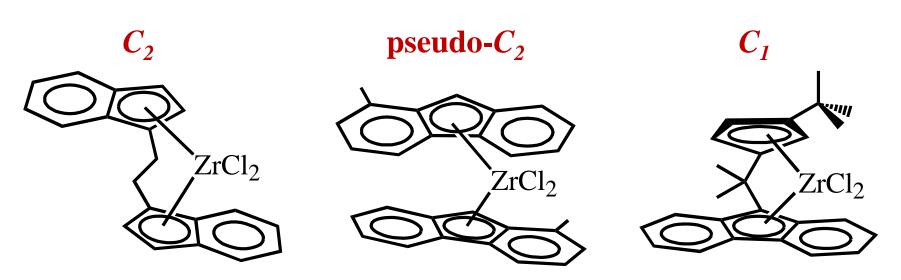


ansa-zirconocenes catalysts of C_2 symmetry

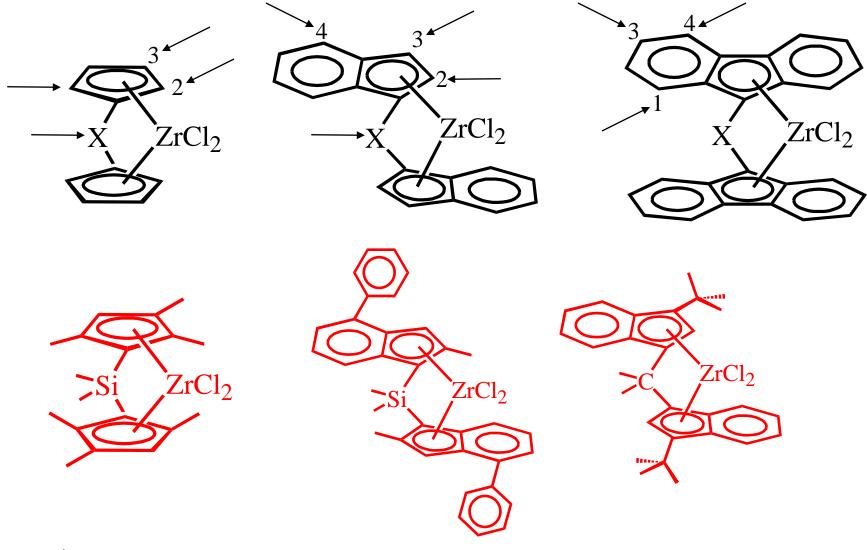


DIFFERENT INSERTION WAYS FOR PROPYLENE¹

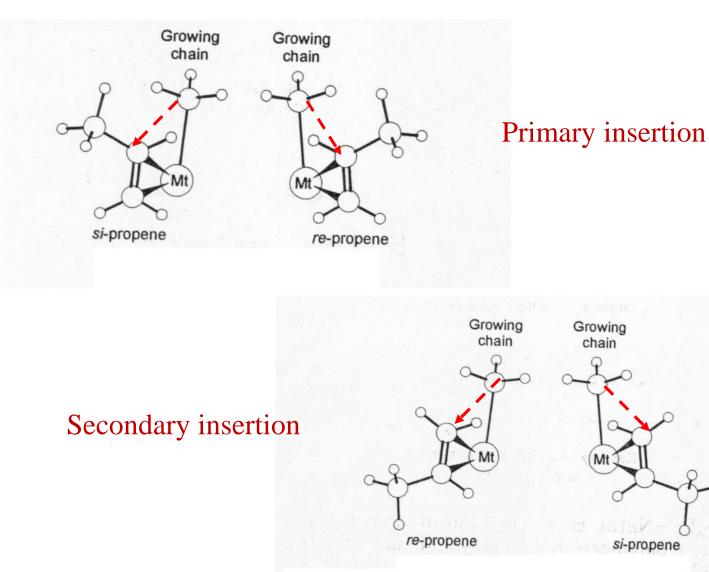

The key-in-the-lock model: one lock, one key

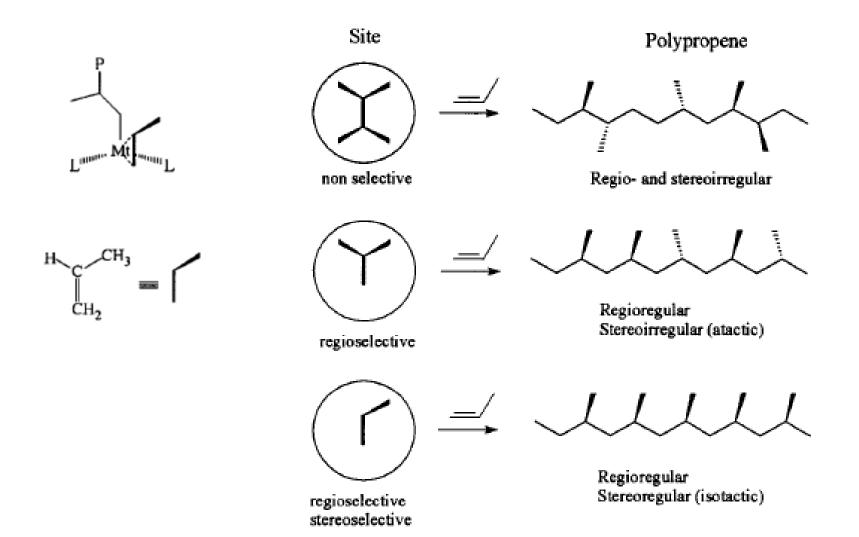


The key-in-the-lock model: two locks, one key

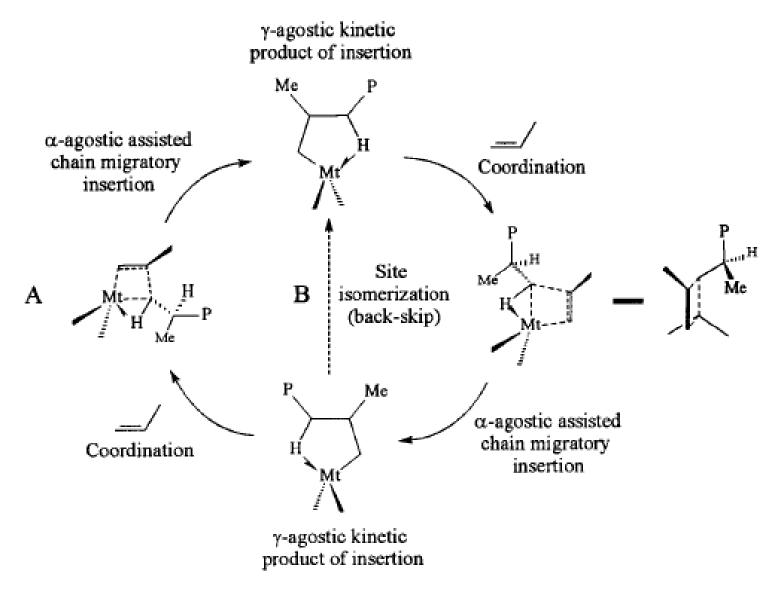

THE ELEMENTS OF CHIRALITY¹


propylene enantioface

growing chain

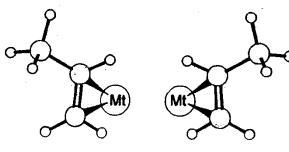


si-coordinated propene


re-coordinated propene

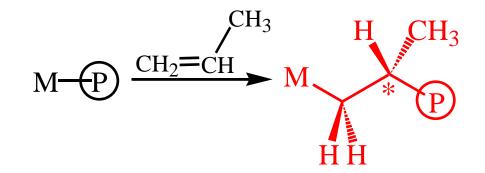


enantiomorphic site

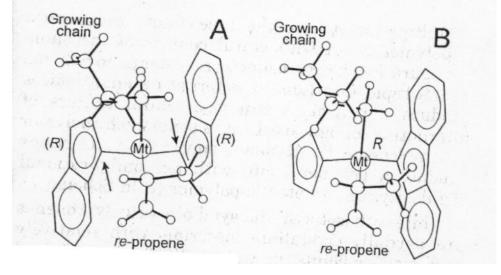


CHIRAL INDUCTION FOR THE PRIMARY INSERTION¹

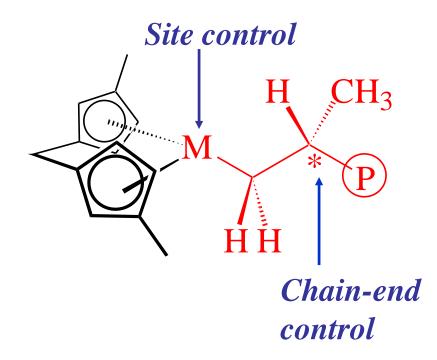


CHIRAL INDUCTION FOR THE PRIMARY INSERTION¹

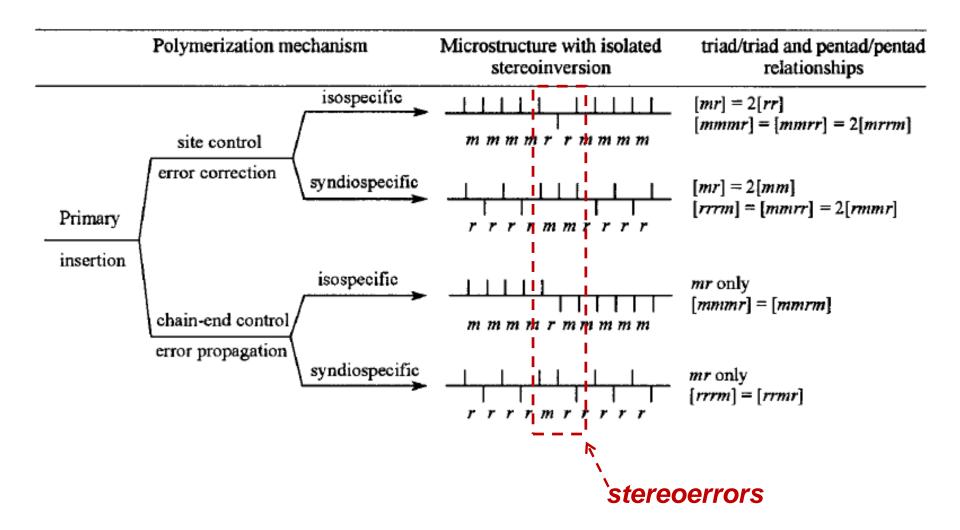



THE CATALYTIC CYCLE

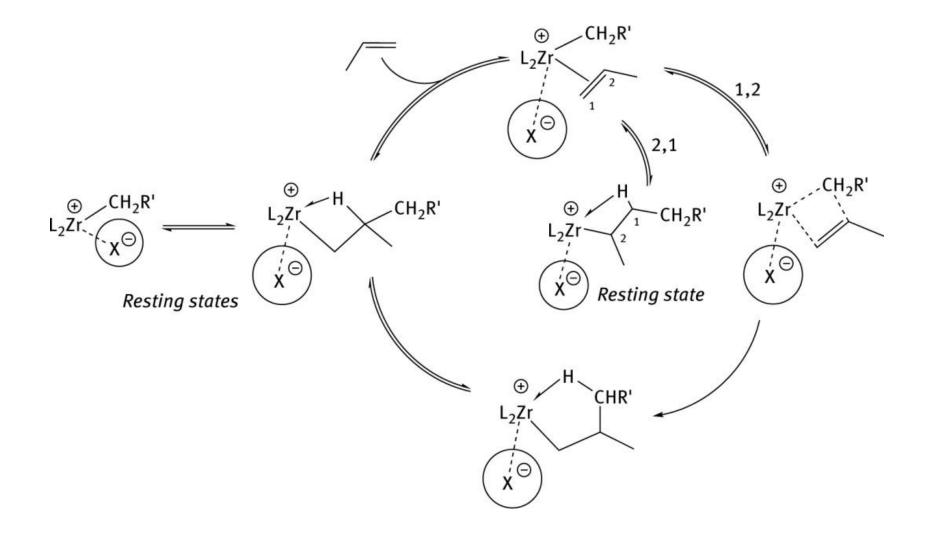

SYNDIOSPECIFIC Catalyst

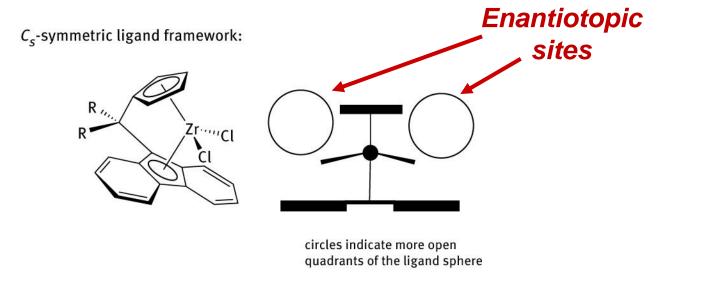


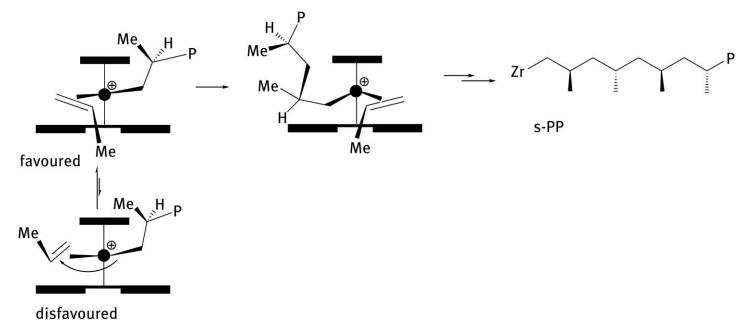


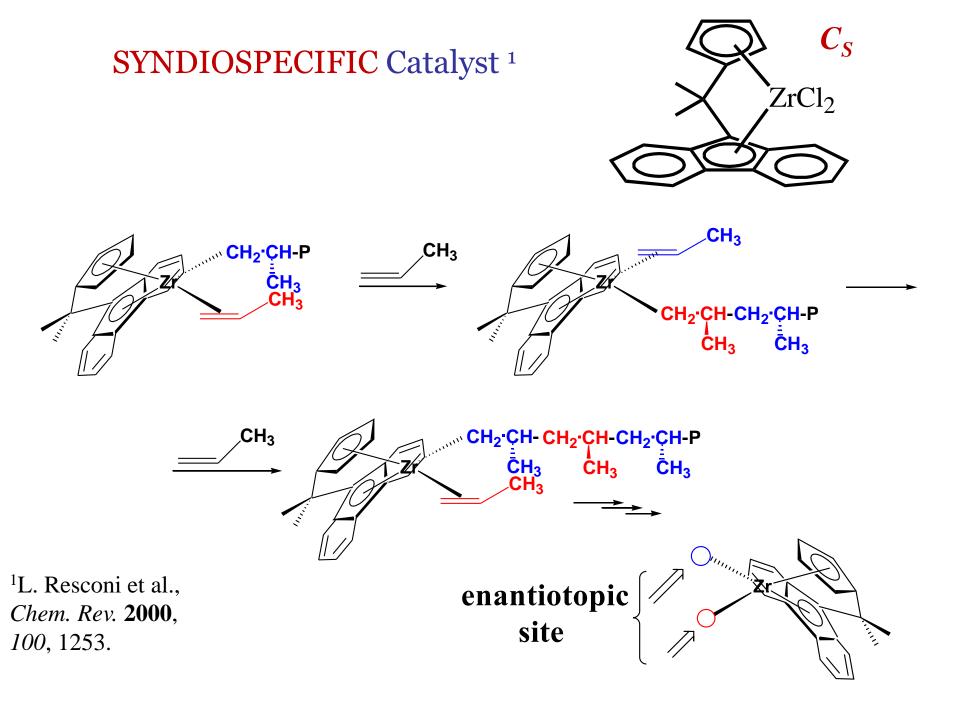

ISOSPECIFIC Catalyst


C₂-symmetric ligand framework: Schematic front viewCl Cl M = Ti, Zr, Hfcircles indicate more open quadrants of the ligand sphere $Z = SiMe_2$, CMe_2 , CH_2CH_2 , etc. P Me Ð

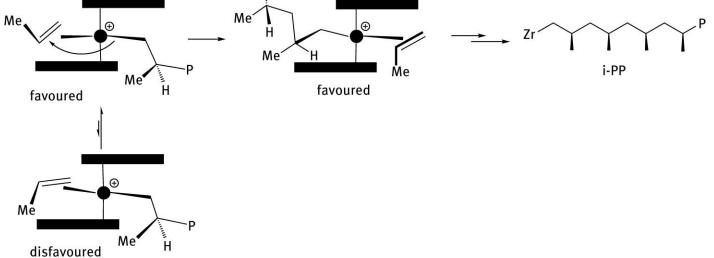

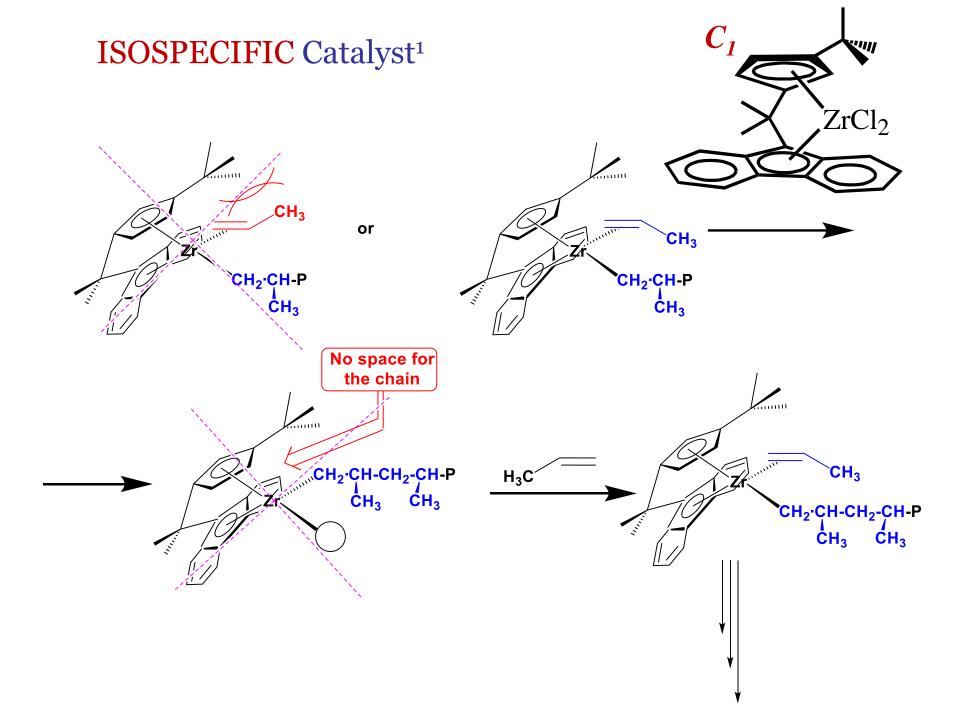


Catalyst for the synthesis of *polypropylene with stereoblocks*

Catalyst in chiral conformation

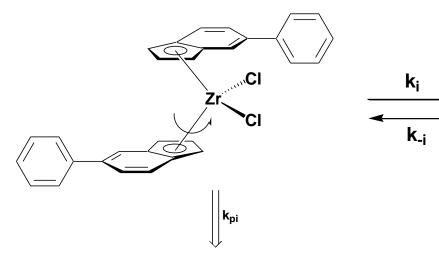

Isotactic block


Catalyst in meso conformation





Atactic block

Catalyst for the synthesis of *polypropylene with stereoblocks*

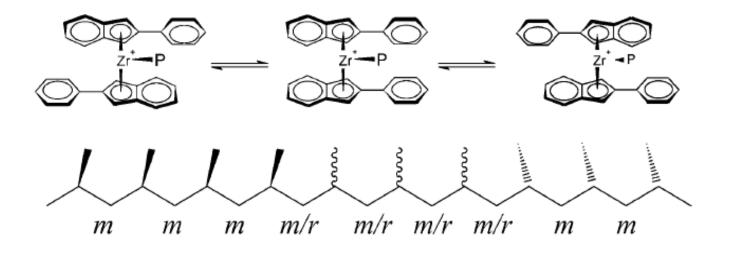

Trend of productivity: $MeB(C_6F_5)_3^- \ll B(C_6F_5)_4^- \simeq MAO$

STEREOSPECIFIC Catalysts ¹: a summary


 $TiCl_3 \longrightarrow$ The Ti isospecific sites are featured by C₂ symmetry (Allegra, 1971)

Ticl₂ \longrightarrow Brintzinger, 1982 \longrightarrow Isotactic PP (Ewen, 1984)


racemic complex isotactic PP

meso complex


→ atactic PP

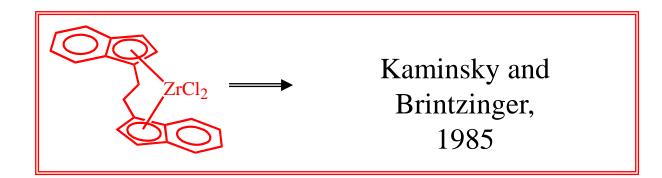

Propylene polymerization catalyzed by NON metallocene complexes

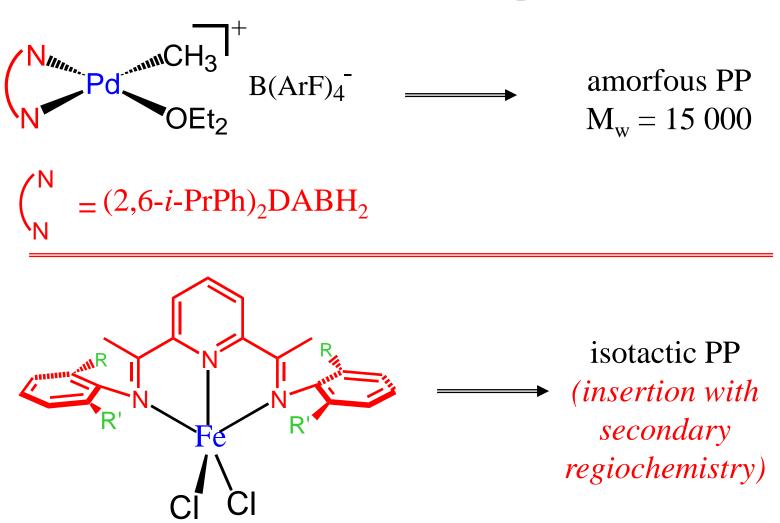

¹S. D. Ittel et al., *Chem. Rev.* **2000**, *100*, 1169.

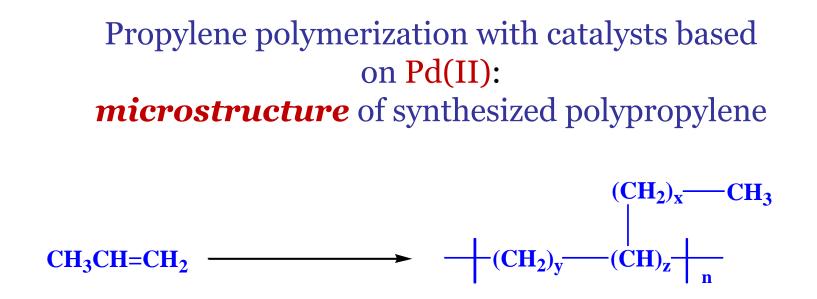

Polymer *microstructure* might be related to the following features of the catalyst:

• alkene insertion might occur with both primary and secondary regiochemistry;

• the catalyst can move along the polymer chain in both directions.